

Springer Proceedings in Materials

Mariappan Rajan
Krishnan Anand
Anil Chuturgoon *Editors*

Proceedings of the International Conference on Nanomedicine (ICON—2019)

 Springer

Springer Proceedings in Materials

Series Editors

Arindam Ghosh, Department of Physics, Indian Institute of Science, Bangalore, India

Daniel Chua, Department of Materials Science and Engineering,
National University of Singapore, Singapore, Singapore

Flavio Leandro de Souza, Universidade Federal do ABC, Sao Paulo, São Paulo, Brazil

Oral Cenk Aktas, Institute of Material Science, Christian-Albrechts-Universität zu Kiel, Kiel, Schleswig-Holstein, Germany

Yafang Han, Beijing Institute of Aeronautical Materials, Beijing, Beijing, China
Jianghong Gong, School of Materials Science and Engineering,
Tsinghua University, Beijing, Beijing, China

Springer Proceedings in Materials publishes the latest research in Materials Science and Engineering presented at high standard academic conferences and scientific meetings. It provides a platform for researchers, professionals and students to present their scientific findings and stay up-to-date with the development in Materials Science and Engineering. The scope is multidisciplinary and ranges from fundamental to applied research, including, but not limited to:

- Structural Materials
- Metallic Materials
- Magnetic, Optical and Electronic Materials
- Ceramics, Glass, Composites, Natural Materials
- Biomaterials
- Nanotechnology
- Characterization and Evaluation of Materials
- Energy Materials
- Materials Processing

To submit a proposal or request further information, please contact one of our Springer Publishing Editors:

China: **Mengchu Huang** (mengchu.huang@springer.com)

India: **Akash Chakraborty** (akash.chakraborty@springernature.com)

Europe: **Mayra Castro** (mayra.castro@springer.com)

America: **Michael Luby** (Michael.luby@springer.com)

More information about this series at <http://www.springer.com/series/16157>

Mariappan Rajan · Krishnan Anand ·
Anil Chuturgoon
Editors

Proceedings of the International Conference on Nanomedicine (ICON-2019)

Editors

Mariappan Rajan
Department of Natural
Products Chemistry
Madurai Kamaraj University
Madurai, India

Krishnan Anand
School of Laboratory Medicine
and Medical Sciences
University of KwaZulu-Natal
Durban, South Africa

Anil Chuturgoon
School of Laboratory Medicine
and Medical Sciences
University of KwaZulu-Natal
Durban, South Africa

ISSN 2662-3161

ISSN 2662-317X (electronic)

Springer Proceedings in Materials

ISBN 978-3-030-25134-5

ISBN 978-3-030-25135-2 (eBook)

<https://doi.org/10.1007/978-3-030-25135-2>

© Springer Nature Switzerland AG 2019

This work is subject to copyright. All rights are reserved by the Publisher, whether the whole or part of the material is concerned, specifically the rights of translation, reprinting, reuse of illustrations, recitation, broadcasting, reproduction on microfilms or in any other physical way, and transmission or information storage and retrieval, electronic adaptation, computer software, or by similar or dissimilar methodology now known or hereafter developed.

The use of general descriptive names, registered names, trademarks, service marks, etc. in this publication does not imply, even in the absence of a specific statement, that such names are exempt from the relevant protective laws and regulations and therefore free for general use.

The publisher, the authors and the editors are safe to assume that the advice and information in this book are believed to be true and accurate at the date of publication. Neither the publisher nor the authors or the editors give a warranty, expressed or implied, with respect to the material contained herein or for any errors or omissions that may have been made. The publisher remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

This Springer imprint is published by the registered company Springer Nature Switzerland AG
The registered company address is: Gewerbestrasse 11, 6330 Cham, Switzerland

Contents

Green Synthesis of Silver Nanoparticles Using <i>Ledebouria Revoluta</i> Bulb Extract and Its Biological Activity	1
R. Aswini, S. Meimozhi, R. Tamilmozhi, M. Kowsalya, and S. Murugesan	
Precision Medicine: A Personalized Treatment from Your Gene	11
P. K. Balasubramani, K. Preetha, and M. Aswanth Harish	
Ultrasonic Studies on Molecular Interaction and Their Excess Properties of Ternary Liquid Mixtures of 2-Nitroanisole and 1-Propanol in n-Hexane at Different Temperatures 303, 308 and 313k	18
J. Edward Jeyakumar, S. Chidambara Vinayagam, and J. Senthil Murugan	
Thermal and Physical Properties of Some Deep Eutectic Solvents	34
P. G. Ramesh and D. Ilangeswaran	
Apoptotic Activity in Cervical Cancer HeLa Cell Lines Treated with Chitosan Nanoconjugated Drug Doxorubicin – as Nanocarrier for Drug Delivery	42
M. R. Kamala Priya and Priya R. Iyer	
One Step Synthesis of Reduced and <i>Moringa oleifera</i> Treated Graphene Oxide: Characterization and Antibacterial Studies	54
R. Kanish Siddarth, M. Manopriya, G. Swathi, G. Vijayvenkataraman, and K. R. Aranganayagam	
Encapsulation of Amphotericin B into Quercetin Based Silver Nanoparticles: Preparation, Characterization and Preliminary Investigation of Antiparasitic Activity	63
Anukragah Sundar, Sankarganesh Arunachalam, Sridhar Jayavel, and Lakshmanan Muthulakshmi	

Dual Delivery of Antibiotic and Antiresorptive Drugs by Hydroxyapatite-Chitosan Composite Nanocarrier for the Treatment of Osteomyelitis	72
S. Ram Prasad, A. Jayakrishnan, and T. S. Sampath Kumar	
The Impact of Gold Nanoparticles with Low Energy Irradiation Treatment on Temperature Induction and Cell Viability of Breast Cancer Cell	86
R. Sowmiya, Tanakorn Osotchan, and Dakrong Pissuwan	
Green Synthesis of Silver Nanoparticles from De-oiled Rhizomes of <i>Curcuma longa</i> L. and Its Biomedical Potential	94
Sinthia Ganesan, Palanichamy Mehalingam, and Govindan Sadasivam Selvam	
<i>In-Vitro</i> Wound Healing and Release Kinetics of β-Cyclodextrin Encapsulated Curcumin Loaded Carrageenan Hydrogel Film: An Efficient Wound Dressing Material	107
Aswni Sundara Rajan, Kerensa Miriam Sheen, Balaji Sadhasivam, and Nachimuthu Saraswathy	
Phytosynthesis of Silver Nanoparticles Using <i>Rhynchosia heynei</i> Wight & Arn Leaf Extract: Characterization and <i>in Vitro</i> Assessment of Antimicrobial, Antioxidant and Anticancer Activities	120
S. Soneya, N. Vasudeva Reddy, K. V. Saritha, Venkata Subbaiah Kotakadi, and T. Vijaya	
Acoustical and Excess Properties on Ternary Liquid Mixtures of Ortho Methoxy Phenol, 1 Butanol and n-Hexane at Different Temperatures	141
P. S. Syed Ibrahim, S. Chidambaravinayagam, J. Senthil Murugan, and J. Edward Jeyekumar	
A Facile Route for the Fabrication of Nanocomposite by Effective Impregnation Through the Biopolymer Matrix and Its Characterisation	153
T. Uma Rajalakshmi and G. Alagumuthu	
Author Index	163



Green Synthesis of Silver Nanoparticles Using *Ledebouria Revoluta* Bulb Extract and Its Biological Activity

R. Aswini, S. Meimozhi, R. Tamilmozhi, M. Kowsalya,
and S. Murugesan^(✉)

Department of Botany, Periyar University,
Periyar Palkalai Nagar, Salem 636 011, India
drsmbtpu@gmail.com

Abstract. In this present examination explores the viability of silver nanoparticles (AgNPs) green synthesis from bulb extract of *Ledebouria revoluta* as an antitumor specialist utilizing human lung cancer cell line (A549). The AgNPs synthesis was determined by UV-Visible range and it was additionally described by field X-beam diffraction (XRD) and Fourier Transform Infrared Spectroscopy (FTIR) investigation High Resolution Transmission electron microscope (HRTEM) and EDS. The level of dictated by MTT examine. The outcomes demonstrated that green synthesized silver nanoparticles inhibited proliferation of human lung disease cell line A549 with an IC₅₀ esteem 72.65 µg/ml. The antimicrobial exercises of silver nanoparticles were checked against gram positive and gram negative strains utilizing in well diffusion technique. The antibacterial chlorophenicol as the positive control was completed. The outcome demonstrated the silver nanoparticles indicated effective movement against bacterial pathogens and cancer growth action.

Keywords: A549 cell line · MTT assay · Gram positive and gram negative bacteria · *Ledebouria revoluta* bulb extract

1 Introduction

Nanotechnology ways to deal with keep the sicknesses in people and regular products have as of late been expanding enormously and select the physiochemical exercises of nanosized metal particles make it fruitful in normal science and medication [1]. The different potential natural uses of nanoparticles have assumed a noteworthy job in the look for ecofriendly procedure of creating nanoparticles utilizing different biomaterials as the traditional synthetic union includes the utilization of dangerous solvents vitality and high weight which might be hurtful to the ecological fields [2]. Nanoparticles combination by restorative plants demonstrates more preferred standpoint they may improve the antibacterial action of silver nanoparticles in light of the fact that the therapeutically vital bioactive particles present stuck the plants may sticky situation on the outside of the nanoparticles and lessen the silver particles to AgNPs [3, 4]. The phytochemicals present in plant removes have been accounted for to make decrease of metal particles nanoparticles and in the long run devastate the utilization of poisonous synthetic

substances high weight temperature vitality and support of microbial societies [5, 6]. This green union of NPs utilizing phytocompounds as bio-reductants is accomplishing a more noteworthy catalyst [7].

Green combination of nanoparticles is a rising part of nanotechnology in which naturally generous materials like plant leaf concentrate, microbes and organisms these utilized for the synthesis [8]. Silver nanoparticles (AgNPs) have pulled in critical enthusiasm among the developing nanoproducts on account of their exceptional properties and expanding use for different applications in nanomedicine [9]. The silver nanoparticles have pulled in with significant enthusiasm because of their broad pertinence in various research fields, for example, science vitality, medication and catalysis. AgNPs were discovered the size extending from 30 to 60 nm. A silver nanoparticle at various focus was assessed for its antibacterial impact, against different pathogens. Hence silver NPs as an antimicrobial operator appear to be contrasted with antimicrobial, also, few reports show synergistic upgrade of action of anti-microbial with AgNPs. Presently the incorporated silver nano particles from natural items have been generally contemplated by different analysts [10].

The *Ledebouria revoluta* Jessop [Syn: Scillaindica (wright) baker or *Scilla hyacinthina* (Roth) J.F. Macbr and Drimiopsisbotryoids baker [syn: Drimiopsiskirkii baker] are Leafaceous species of the family Asparagaceae The Plant List 2013. Traditionally used medicinal plants have recently attracted the attention of pharmaceutical and scientific communities [11]. Cancer is a standout amongst the most life threatening ailments in which deregulating expansion of strange cells attacks and upsets encompassing tissues [12]. Cancer is an all out malady in which the cell development is forceful and intrusive and metast ordinarily prompting demise [13]. Today cancer is the biggest single reason for death is people and chemoprevention has been a promising anticancer methodologies went for lessening the dismalness and mortality of malignant growth by deferring the procedure of carcinogenesis [14].

The present examination was expected to green combination of silver nanoparticles utilizing bulb extract of *L. revoluta* against cytotoxicity A549 malignant growth cell lines. We have researched the antibacterial movement of integrated nanoparticles fundamental by well dispersion strategies. The impacts of nanoparticles on bacterial development have been additionally broke down by utilizing the base inhibitory fixation strategy.

2 Materials and Methods

2.1 Preparation of Plant Extract

The fresh bulb of *Ledebouria revoluta* gathered from Periyar University grounds. 20 gm of collected fresh bulb was added to 250 ml of refined water and bubbled for 15 min at 60 °C. The prepared aqueous extract was separated through Whatman No. 1 channel paper. The sifted concentrate was put away in cooler at 4 °C.

2.2 Synthesis of AgNPs

For synthesis of AgNPs, 50 ml of the aqueous bulb extract was added to 450 ml of 1 mM silver nitrate (AgNO_3) solution. The blend was kept into dim condition at 24 h. The improvements of AgNPs were considered by visual perception of the shading change from light yellow to deep brown color.

2.3 Characterization of AgNPs

2.3.1 UV-Vis Spectroscopy

The synthesized AgNPs was established by sampling the aqueous component behind the reaction and the absorption maxima was scanned by T80 UV-Vis spectrometer at the wavelength of 200–800 nm.

2.3.2 FTIR Spectroscopy

In the FTIR spectrum, the samples were determined using the model of Perkin Elmer spectrum 1 FTIR spectroscopy, sample range $500\text{--}4000\text{ cm}^{-1}$.

2.3.3 XRD Analysis

The particle size and nature of the AgNPs were determined using XRD. This was carried out using diffraction meter, brucker, Germany model D8 advance model by 30 kV and 30 mA with Cu $\text{K}\alpha$ radians at 2θ angle.

2.3.4 HRTEM Analysis

HRTEM (Model-Tecnai, G2 20 twin) was utilized to study the surface morphology and size of the integrated nanoparticles. For HR-TEM investigation, the example was set up by dissolving 2 mg of the nanoparticles in 10 ml of methanol by sonication process. Two drops of this arrangement were put on the carbon-copper matrices and were permitted to evaporate the dissolvable.

2.3.5 EDS Analysis

The energy dispersive X-ray spectroscopy was performed by a Bruker EDX spectrometer to determine the elemental composition of the samples.

2.4 Antibacterial Activity

The well diffusion method (Anonymous, 1996) was utilized to show the antibacterial properties. Different concentration of the extract (100 $\mu\text{g/ml}$) was set up by AgNPs. The test microorganisms were seeded into particular medium by spread plate strategy 10 μl (10 cells/ml) with the 24 h societies of microbes development in supplement stock. After hardening the channel paper wells (5 mm in distance across) impregnated with the concentrates were put on test living being seeded plates. Chloramphenicol (10 μg) utilized as standard for antibacterial test. The antibacterial test plates were hatched at 37°C for 24 h. The distances across of the restraint zones were estimated in mm.

2.5 Cytotoxicity Activity

2.5.1 Cell Line

The human lung cancer cell line (A549) was obtained from National Centre for Cell Science (NCCS), Pune and grown in Eagles Minimum Essential Medium containing 10% fetal bovine serum (FBS). The cells were maintained at 37 °C, 5% CO₂, 95% air and 100% relative humidity. Maintenance cultures were passaged weekly, and the culture medium was changed twice a week.

Cytotoxicity effect of the AgNPs was measured by the MTT assay [17, 18]. The cells were maintained in DMEM medium, added with 10% of bovine serum at 37 °C in humidity field atmosphere with 5% CO₂. The cells were plated in 96 well a flat bottom tissue culture plates at concentration of approximately 1×10^5 cell s/well and allowed to attach overnight at 37 °C. Then, the cells were incubated by different concentrations of the AgNPs bulb extract of *Ledebouria revoluta* for 48 h. After the incubation, the medium was redundant and 100 µl fresh medium was added with 5 µl of MTT assay (5 mg/ml). After 4 h, the medium added in 100 µl of DMSO to dissolve the Formosan crystals. Then, the absorbance was read at 570 nm in a microliter plate reader. The IC₅₀ value was calculated.

2.5.2 Statistical Analysis

All the measurements were carried out in triplets and the results are expressed as mean $\pm$ SD using on way analysis (ANOVA) through SPSS software.

3 Results and Discussion

3.1 UV-Vis Spectroscopy

The aqueous of *L. revoluta* with watery arrangement of the nitrate (AgNO₃) start to change the shading from yellow to darkish brown shading. It showed the development of AgNPs with decrease of silver particle. The assimilation groups were gotten at 472 nm (Fig. 1). The presence of the dark colored shading was because of excitation of the surface Plasmon vibrations. The arrangement of AgNPs was observed by UV-Visible spectroscopy in the 200–800 nm extend [15]. The result got for UV range for the AgNPs arranged from *P. maderaspatens* is root uncovered the most extreme retention was observed to be at 479 nm.

3.2 FTIR Spectroscopy

The FTIR spectroscopy estimation was concentrated to distinguish the conceivable biomolecules for the development and adjustment of AgNPs. The pinnacles showed up at 3209.55, 2926.01, 1622.13, 1527.62, 1217.08, 1014.56 cm⁻¹ (Fig. 2). The solid assimilation tops at 3209.55 cm⁻¹ uncovers the nearness of O-H extending liquor and phenol gathering. The pinnacle 2926.01 cm⁻¹ maybe allotted to alkenes is clear from C-H extending the pinnacle seemed 1622.13 cm⁻¹ was relegated to the extending C = O of gathering amide. The pinnacle acquired at 1527.62 cm⁻¹ N-O extending in nitro gathering. The pinnacle got at 1217.08 cm⁻¹ shows fragrant C-N. The pinnacle acquired at 1014.56 cm⁻¹ compares to C-O extending ether gathering.

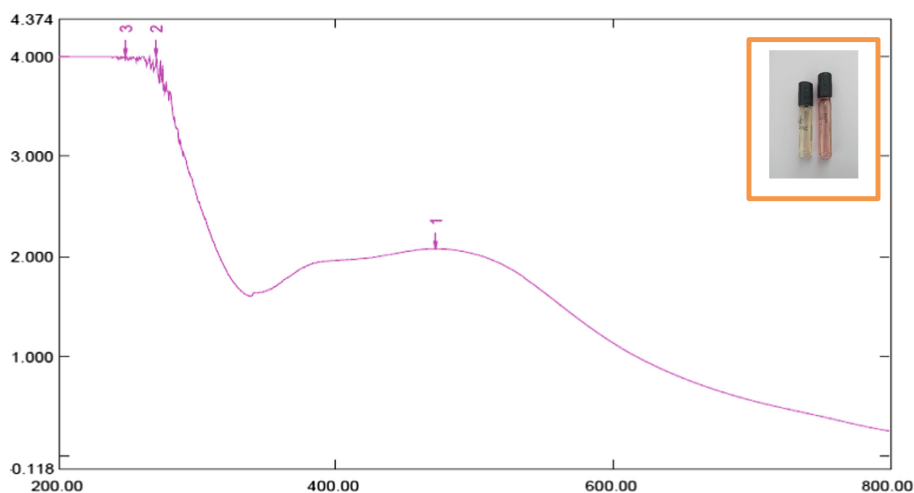


Fig. 1. UV-Vis absorption spectra of silver nanoparticle synthesized extract (AgNPs)

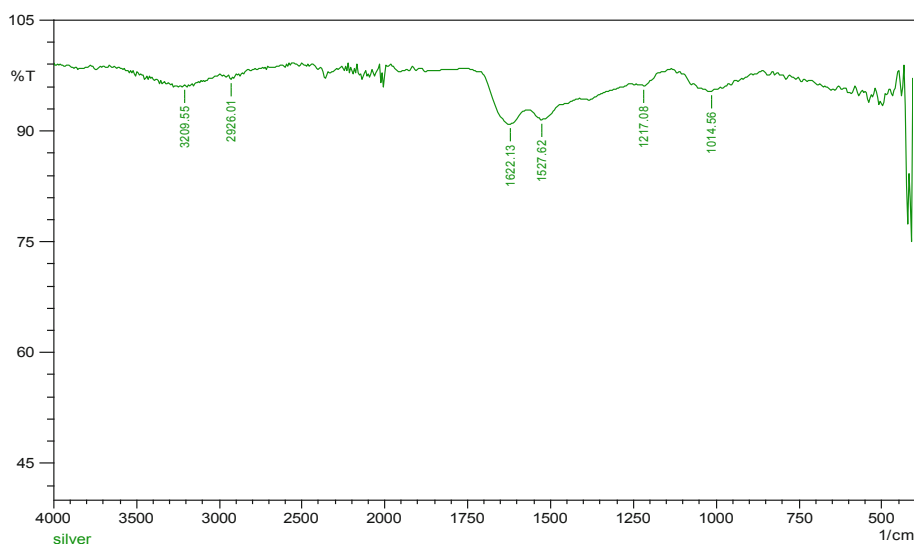


Fig. 2. FT-IR spectrum of silver nanoparticles synthesized by *Ledebouria revoluta* bulb part

3.3 XRD Analysis

The X-ray powder diffraction designs shows distinctive precious stone planes namely (210), (122), (111), (231), (142), (241), (220) and (311) of the nanometals, which relates to the crests with two theta esteems 27.91, 33.45, 46.56, 54.92, 57.32, 64.50, 77.32, same outcome uncovered (Fig. 3). Unidentified crystalline pinnacles (27.89, 32.30, 46.26, 54.79) are likewise clear in numerous works in which the XRD design incorporates the important 20 territory [16].

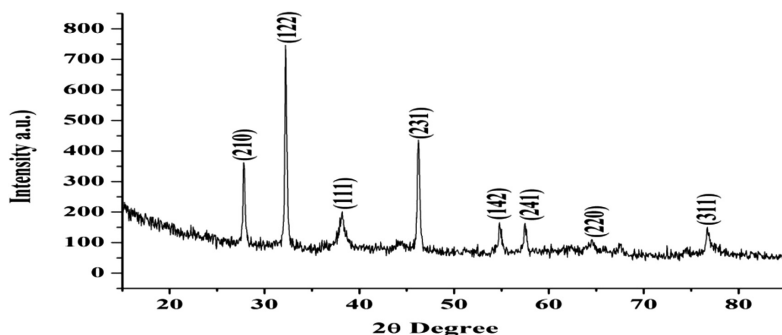


Fig. 3. X-ray diffraction patterns of synthesized AgNPs by *Ledebouria revoluta* bulb part

3.4 HRTEM and EDS

The morphology, measurement and circulation of the integrated nanoparticles were envisioned utilizing high goals transmission electron minuscule investigation. In the investigation dispersive spectroscopy (EDS) of the AgNPs the nearness of essential metal flag was affirmed (Fig. 5). HRTEM picture is the clear that the morphology of silver nanoparticles round shape (Fig. 4).The silver nanoparticles have circular geometry with a normal measurement of 18.05 ± 4.73 nm [17].

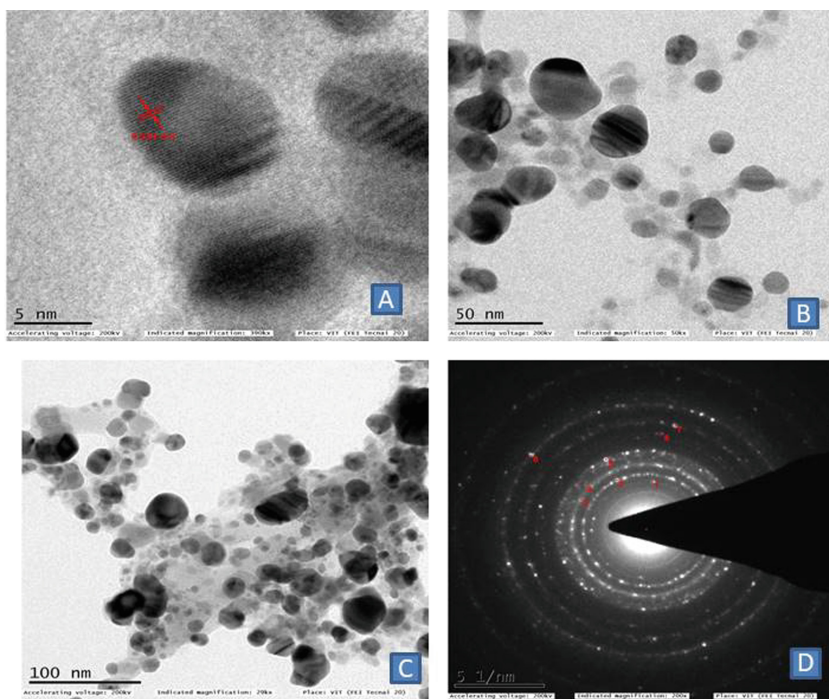


Fig. 4. High resolution transmission electron microscopic images of silver nanoparticles at different magnification. A-C size distribution histogram of TiO₂NPs and (D) SAED pattern.

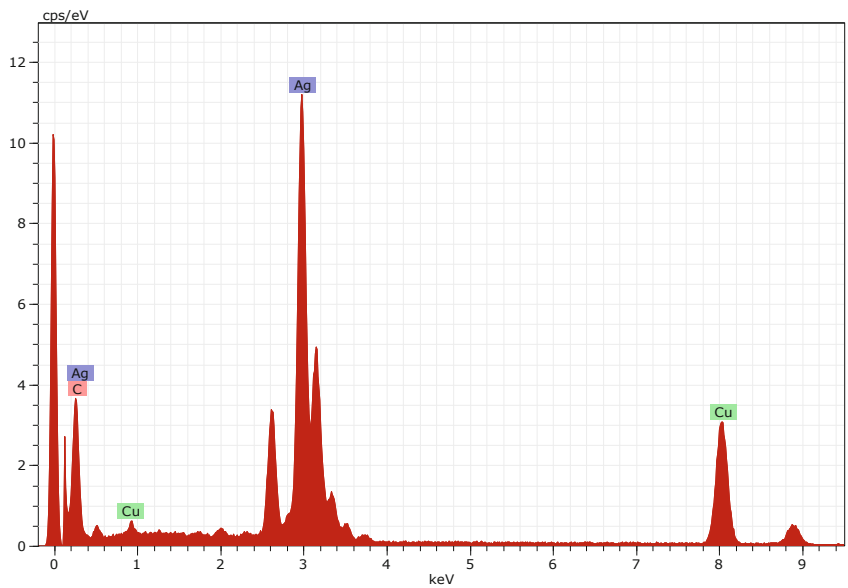


Fig. 5. EDS spectroscopy displays the purity and chemical composition of the AgNPs

3.5 Antibacterial Activity

The antibacterial activity test after effects of AgNo3 against various gram positive and negative microorganism were appeared Tables 1 and 2. Among utilizing three gram negative microbes the high restraint development in *Bacillus cerus* 5.66 ± 2.49 in 25hl (Fig. 6). In gram positive microorganisms the *Salmonella typhi* has been most astounding hindrance as 6 ± 2.44 in 25 μ l. He revealed as the comparable outcome that the AgNPs has been great antibacterial movement [18].

Table 1. Gram positive bacterial activity of different concentration of Silver nanoparticles

S. no	Pathogenic bacteria	AgNPs extract Zone of inhibition (mm)				Standard (Chloramphenicol)
		10 μ l	15 μ l	20 μ l	25 μ l	
1	<i>Bacillus cerus</i>	0.33 ± 0.47	3.33 ± 1.24	3.66 ± 1.69	5.66 ± 2.49	3.66 ± 1.69
2	<i>Clostridium tetani</i>	2.33 ± 0.47	3.33 ± 0.94	3.33 ± 1.24	4.33 ± 1.88	3.66 ± 1.69
3	<i>Mycobacterium tuberculosis</i>	0.33 ± 0.47	1.66 ± 0.94	3 ± 1.41	4.33 ± 1.24	4.33 ± 2.05

Table 2. G negative bacterial activity of different concentration of Silver nanoparticles

S. no	Pathogenic bacteria	AgNPs extract Zone of inhibition (mm)				Standard (Chloramphenicol)
		10 μ l	15 μ l	20 μ l	25 μ l	
1	<i>Vibrio cholera</i>	1.33 ± 1.24	2 ± 1.63	4 ± 1.4	4 ± 1.69	4.33 ± 0.94
2	<i>Salmonella typhi</i>	0.33 ± 0.47	2.66 ± 0.47	2.33 ± 1.24	6 ± 2.44	4.66 ± 1.24
3	<i>Klebsiella nemoniae</i>	0.66 ± 0.47	0.33 ± 0.47	2.66 ± 0.94	3.33 ± 1.24	5.66 ± 1.24

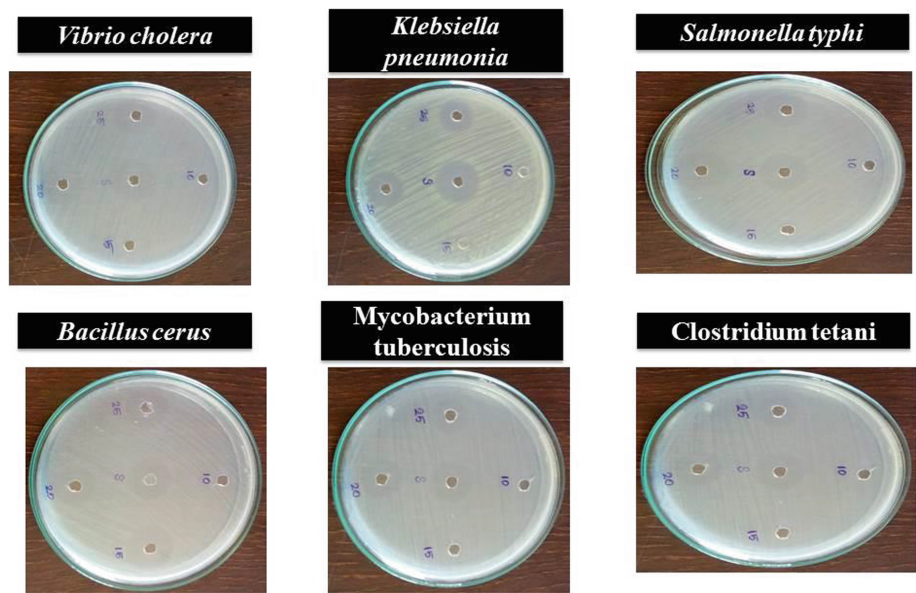


Fig. 6. Zone of inhibition of gram-negative bacterial strains using silver nanoparticles of different concentrations

3.6 Cytotoxicity Analysis of A549 Cell Line

The cytotoxicity of the AgNPs separate was against A549 cell line by MTT measure Fig. 7 demonstrate the cytotoxicity of AgNPs against A549 cell line. The cytotoxicity sway on cell development was inspected at various fixation (6.25, 12.5, 25, 50 and 100 µg) appeared in Table 3. The level of disease cell development restraint was observed to be high with the expanding the centralization of AgNPs the IC₅₀ for *L. revoluta* was recorded at 72.65 µg/ml against A549 cells at 100 µg focus (Fig. 7). Detailed the AgNPs remove A549 cell line utilizing *S. aromatium* AgNPS extract [19].

Table 3. AgNPs treated A549 lung cancer cells

Conc	6.25 µg	12.5 µg	25 µg	50 µg	100 µg	Cont
ABS	0.038	0.068	0.141	0.193	0.245	0.425
	0.034	0.065	0.143	0.192	0.247	0.422
	0.033	0.066	0.143	0.192	0.243	0.425
Avg	0.035	0.066333	0.142333	0.192333	0.245	0.424
					IC ₅₀ value	72.65 µg/ml

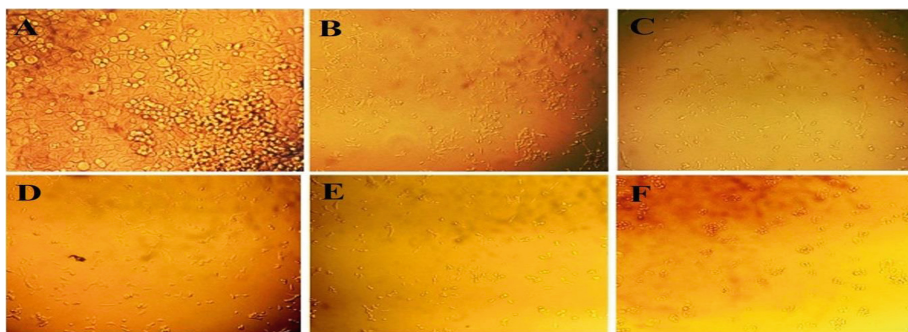


Fig. 7. Morphology of control and AgNPs treated A549 lung cancer cells. A. Control, B. IC₅₀ Concentration (6.5 µg/ml), C. IC₅₀ Concentration (12.5 µg/ml), D. IC₅₀ Concentration (25 µg/ml), E. IC₅₀ Concentration (50 µg/ml), F. IC₅₀ Concentration (100 µg/ml).

4 Conclusion

Plant extract assisted green synthesis of silver nanoparticles. The synthesized silver nanoparticles were characterized viz., UV-Vis, XRD, FTIR, TEM and EDS. Their biological significance was proven by efficient in bacterial activity and A549 cell line.

References

1. Jo, Y.K., Kim, B.H., Jung, G.: Antifungal activity of silver ions and nanoparticles on phytopathogenic fungi. *Plant Dis.* **93**, 1037–1043 (2009)
2. Singaravelu, G., Arokiyarnary, J.S., Kumar, V.G., et al.: A novel extracellular synthesis of monodisperse gold nanoparticles using marine algae, *Sargassum wightii* Greville. *Colloids Surf. B* **57**(1), 97–101 (2007)
3. Popescu, M., Velea, A., Lorinczi, A.: Biogenic production of nanoparticles. *Dig. J. Nanometer Biostruct.* **5**(4), 1035–1040 (2010)
4. Baruwati, B., Polshettiwar, V., Varma, R.S.: Glutathione promoted expeditious green synthesis of silver nanoparticles in water using microwaves. *Green Chem.* **11**, 926–930 (2009)
5. Jha, A.K., Prasad, K., Kulkarni, A.R.: Plant system: nature's nanofactory. *Colloids Surf. B Biointer.* **73**, 219–223 (2009)
6. Annamalai, N., Thavasi, R., Vijayalakshmi, S., Balasubramanian, T.: A novel thermostable and halostable carboxymethylcellulase from marine bacterium *Bacillus licheniformis* AUO. *World J. Microbial. Biotechnol.* **27**, 2111–2115 (2011)
7. Raj, M., Yadav, A.: Plants are potential synthesizer of precious metal nanoparticles; Progress and prospects. *IET Nanobiotechnol.* **7**(3), 117 (2013)
8. Krishnaraj, C., Jagan, E.G., Rajasekar, S., Kalaiselvan, P.T., Mohan, N.: Synthesis of silver nanoparticles using *Acalypha indica* leaf extract and its Antibacterial activity against water borne pathogens. *Colloids Surf. B Biointer.* **76**, 50–56 (2010)
9. Muleva, E., Ahmed, A.S., Sipamla, A.M., Mtunzi, F.M.: Free radical scavenging and antibacterial activity crude extracts from selected plants of medicinal value used in Zululand. *Pak. J. Nutr.* **13**(1), 38–42 (2014)

10. Gennari, C., Castoldi, D., Sharon, O.: Natural products with taxol like anti-tumor activity: synthetic approaches to eleutherobin and dictyostain. *Pure Appl. Chem.* **79**, 173–180 (2007)
11. Guarino, M., Rubino, B., Ballabio, G.: The role of epithelial mesenchymal transition in cancer pathology. *Pathology* **39**, 305–318 (2007)
12. Kaufman, S.H., Earnshaw, W.C.: Induction of apoptosis by cancer chemotherapy. *Exp. Cell Res.* **256**, 42–49 (2000)
13. Santhosh, S.B., Ragavenderan, C., Natarajan, D.: Spectral and HRTEM analyses of *Annona muricata* leaf extract mediated silver nanoparticles and its Larvicidal efficacy against three mosquito vectors *Anopheles stephensi*, *Culex quinquefasciatus*, and *Aedes aegypti*. *J. Photochem. Photobiol. B: Biol.* 1011–1344 (2015)
14. Kumar, R., Roopan, S.M., Prabhakaran, A., Khanna, V.G., Chakroborty, S.: Agricultural waste *Annona squamosa* peel extract, biosynthesis of silver nanoparticles *Spectrochim. Acta Part B* **90**, 173–176 (2012)
15. Francis, S., Joseph, S., Koshy, E.P., Mathew, B.: Synthesis and characterization of multifunctional gold and silver nanoparticles using leaf extract of *Naregamia alata* and their applications in the catalysis and control of mastitis. *New J. Chem.* **41**, 14288–14298 (2017)
16. Venugopal, K., Rather, H.A., Rajagopal, K., Shanthi, M.P., Sheriff, K., Llliyas, M., Manikandan, E., Uvarajan, S.: Synthesis of silver nanoparticles (AgNPs) for anticancer activities (MCF 7 breast and A549 lung cell lines) of the crude extract of *Syzygium aromaticum*. *J. Photochem. Photobiol. B: Biol.* **167**, 282–289 (2017)
17. Mosmann, T.: Rapid colorimetric assay for cellular growth and survival: application to proliferation and cytotoxicity assays. *J. Immunol. Methods* **65**, 55–63 (1983)
18. Monks, A., Scudiero, D., Skehan, P., Shoemaker, R., Paull, K., Vistica, D., Hose, C., Langley, J., Cronise, P., Vaigro-Wolff, A., Gray-Goodrich, M., Campbell, H., Mayo, J., Boyd, M.: Feasibility of high flux anticancer drug screen using a diverse panel of cultured human tumour cell lines. *J. Nat. Cancer Inst.* **83**, 757–766 (1991)