




# CONTACT LENSES

*Materials, Chemicals,  
Methods and Applications*

*Johannes Karl Fink*

 Scrivener  
Publishing

WILEY

# Table of Contents

[Cover](#)

[Title Page](#)

[Copyright](#)

[Preface](#)

[Acknowledgements](#)

[1 Types of Lenses](#)

[1.1 History of Contact Lenses](#)

[1.2 Materials](#)

[1.3 Monomers](#)

[1.4 Soft Lenses](#)

[1.5 Water Absorbable Formulations](#)

[1.6 Bandage Contact Lenses](#)

[1.7 Functional Contact Lenses](#)

[1.8 Scleral Contact Lenses](#)

[1.9 Multifocal Contact Lenses](#)

[1.10 Augmented Reality Contact Lens Systems](#)

[1.11 Siloxane Macromers](#)

[1.12 Oxygen-Permeable Lenses](#)

[1.13 Natural Protein Polymer Contact Lenses](#)

[1.14 Ultrathin Coating](#)

[1.15 Anti-Biofouling Contact Lenses](#)

[1.16 Drug Delivery via Hydrogel Contact Lenses](#)

[1.17 Simulation Methods](#)

[References](#)

[2 Fabrication Methods](#)

[2.1 Computer-Aided Contact Lens Design and Fabrication](#)

[2.2 Contact Lenses with Selective Spectral Blocking](#)

[2.3 Colored Contact Lenses](#)

[2.4 Decentered Contact Lenses](#)

[2.5 Stabilized Contact Lenses](#)

[2.6 Additive Manufacturing](#)

[2.7 Mold Process](#)

[2.8 Reactive Ion Etching](#)

[2.9 Electrospinning](#)

[2.10 Rigid Plastic Lenses](#)

[2.11 Soft Plastic Lenses](#)

[2.12 Coating Methods](#)

[2.13 Disinfection of Contact Lenses](#)

[2.14 Integrated Microtubes](#)

[2.15 Injection Molding](#)

[2.16 Handling Tools](#)

[References](#)

### [3 Properties](#)

[3.1 Ophthalmic Compatibility Requirements](#)

[3.2 Standards](#)

[3.3 Eye Model with Blink Mechanism](#)

[3.4 Assessment of Cytotoxic Effects](#)

[3.5 Special Functions](#)

[3.6 Cleaning of Contact Lenses](#)

[3.7 Biofouling](#)

[3.8 Wettability](#)

[3.9 Material Properties and Antimicrobial Efficacy](#)

[3.10 Microscopic Examination](#)

[3.11 Schirmer Tear Test](#)

[3.12 Ocular Surface Disease Index Test](#)

[3.13 Corneal Fluorescein Staining Test](#)

[3.14 Ion Permeability](#)

[3.15 Hydrodell Water Permeability Technique](#)

[3.16 Oxygen Permeability and Transmissibility](#)

[3.17 Optical Biometer](#)

[References](#)

#### [4 Drug Delivery](#)

[4.1 Basic Issues](#)

[4.2 Methodologies for the Design of Therapeutic Contact Lenses](#)

[4.3 Hydrogels](#)

[4.4 Contact Lens Gels](#)

[4.5 Molecularly Imprinted Contact Lenses](#)

[4.6 Special Drugs](#)

[References](#)

#### [5 Medical Problems](#)

[5.1 Eye Diseases](#)

[5.2 Corneal Edema](#)

[5.3 Presbyopia and Myopia Control](#)

[5.4 Toxic Soft Lenses](#)

[5.5 Disinfection Agents](#)

[5.6 Silicone Hydrogels](#)

[5.7 Limbal Stem Cell Deficiency](#)

[5.8 Computer Vision Syndrome](#)

[5.9 Dry Eye Problems](#)

[5.10 Orthokeratology](#)

[References](#)

[Index](#)

[Acronyms](#)

[Chemicals](#)

[General Index](#)

[End User License Agreement](#)

## List of Illustrations

### Chapter 1

[Figure 1.1 Monomers for side-chain-linked amino acids.](#)

[Figure 1.2 Compounds for a block copolymer.](#)

[Figure 1.3 Hydrophilic methacrylamide-based monomers.](#)

[Figure 1.4 Monomers for hydrophilic polymers.](#)

[Figure 1.5 Bisacrylamide monomers.](#)

[Figure 1.6 Polyfunctional methacrylate compounds.](#)

[Figure 1.7 Hydrophobic monomers.](#)

[Figure 1.8 Hydrophilic monomers.](#)

[Figure 1.9 Hydrophobic strengthening monomers.](#)

[Figure 1.10 Crosslinking monomers.](#)

[Figure 1.11 Monomers and comonomers.](#)

[Figure 1.12 Azo initiators.](#)

[Figure 1.12 \(cont\) Peroxy initiators.](#)

[Figure 1.12 \(cont\) Photoinitiators.](#)

[Figure 1.12 \(cont\) Photoinitiators.](#)

[Figure 1.13 Tinting agents.](#)

[Figure 1.13 \(cont\) Tinting agents.](#)

[Figure 1.14 2-Alkenyl azlactones.](#)

[Figure 1.14 \(cont\) Cycloalkyl azlactones.](#)

[Figure 1.15 2-Isopropenyl-4,4-dimethyl-2-oxazolin-5-one.](#)

[Figure 1.16 \*n\*-Nonanol.](#)

[Figure 1.17 Diethylene glycol monoethyl ether.](#)

[Figure 1.18 Methyl enanthate or Methyl heptanoate.](#)

[Figure 1.19 3-\[Tris\(trimethylsiloxy\)silyl\]propyl methacryloyloxyethyl succinate.](#)

[Figure 1.20 Monomers for telechelic macromonomers \(20\).](#)

[Figure 1.21 Nucleating agents \(31\).](#)

[Figure 1.22 Cross-sectional view of a contact lens mold assembly \(31\).](#)

[Figure 1.23 Synthesis of \*N\*-carbomethoxymethyl-\*N\*-methacryloylamidopropyl-\*N,N\*-dime...](#)

[Figure 1.24 Sugars in hyaluronic acid.](#)

[Figure 1.25 Crosslinking agents.](#)

[Figure 1.26 Monomers.](#)

[Figure 1.27 Poly\(siloxane\) monomers.](#)

[Figure 1.28 Trifluoromethanesulfonic acid.](#)

[Figure 1.29 Drugs.](#)

[Figure 1.30 Target biomarkers.](#)

[Figure 1.30 \(cont\) Target biomarkers.](#)

[Figure 1.31 Prodan \(1-\(6-\(Dimethylamino\)naphthalen-2-yl\)propan-1-one\).](#)

[Figure 1.32 Synthesis of Quin-C18.](#)

[Figure 1.33 Block diagram of sensor \(60\).](#)

[Figure 1.34 Hormones.](#)

[Figure 1.35 Chipless functional contact lens \(61\).](#)

[Figure 1.36 Electronic contact lens system \(65\).](#)

[Figure 1.37 Accessory device \(65\).](#)

[Figure 1.38 Beam pattern generated by an accessory device \(65\).](#)

[Figure 1.39 Lens manufacturing system \(103\).](#)

[Figure 1.40 4-\(Phenyldiazenyl\) phenyl methacrylate.](#)

[Figure 1.41 UV-blocking agents.](#)

[Figure 1.42 Silicone monomers.](#)

[Figure 1.43 Monomers for non-silicone hydrogels.](#)

[Figure 1.44 Crosslinking agents.](#)

[Figure 1.45 Catalysts.](#)

[Figure 1.46 Hydrophilic monomers.](#)

[Figure 1.47 Initiators.](#)

[Figure 1.48 Catalysts.](#)

[Figure 1.49 Peroxides.](#)

[Figure 1.49 \(cont\) Peroxides.](#)

[Figure 1.50 Monomers.](#)

[Figure 1.51 Isocyanates.](#)

[Figure 1.51 \(cont\) 1,3,5-Tris\(6-isocyanatohexyl\)biuret.](#)

[Figure 1.52 2-Isocyanatoethyl methacrylate.](#)

[Figure 1.53 Contact lens structure \(128\).](#)

[Figure 1.54 Contact angle of water of a silicone rubber sheet coated by a methan...](#)

[Figure 1.55 Synthesis of 2-methacryloyloxyethyl phosphorylcholine and \(2-methacr...](#)

[Figure 1.56 Bis\(trimethylsilyloxy\)methylsilylpropyl glycerol methacrylate.](#)

[Figure 1.57 Bicinchoninic acid.](#)

[Figure 1.58 4',6-Diamidin-2-phenylindol.](#)

[Figure 1.59 Chitosan structure.](#)

[Figure 1.60 Naphazoline.](#)

[Figure 1.61 2-Methacryloyloxyethyl phosphate.](#)

[Figure 1.62 Ligand concentrations versus naphazoline content.](#)

[Figure 1.63 Monomers for an ophthalmic drug delivery system.](#)

## Chapter 2

[Figure 2.1 Special contact lens \(8\).](#)

[Figure 2.2 Decentered contact lens structure \(16\).](#)

[Figure 2.3 Front of a stabilized contact lens \(17\).](#)

[Figure 2.4 Mold insert \(19\).](#)

[Figure 2.5 Side elevation of a contact lens \(21\).](#)

[Figure 2.6 Contact lens mold assembly \(22\).](#)

[Figure 2.7 1-Vinyl-2-pyrrolidinone.](#)



[Figure 2.8 Monomeric acids for mat-forming polymers.](#)

[Figure 2.9 Comonomers for mat production.](#)

[Figure 2.9 \(cont\) Comonomers for mat production.](#)

[Figure 2.9 \(cont\) Comonomers for mat production.](#)

[Figure 2.10 Hydrophilic monomers.](#)

[Figure 2.11 Crosslinking agents.](#)

[Figure 2.12 Genipin.](#)

[Figure 2.13 Di-sec-butyl peroxy dicarbonate.](#)

[Figure 2.14 Hydrazine salts.](#)

[Figure 2.15 Etidronic acid.](#)

[Figure 2.16 Compounds in isotonic buffered saline solution.](#)

[Figure 2.17 Method of inserting a contact lens \(51\).](#)

## Chapter 3

[Figure 3.1 Benzalkonium Chlorides.](#)

[Figure 3.2 Lens materials.](#)

[Figure 3.3 Diethylenetriamine penta\(methylenephosphonic acid\).](#)

[Figure 3.4 Equilibrium water content vs. monomer content \(84\).](#)

[Figure 3.5 Transparency vs. monomer content \(84\).](#)

[Figure 3.6 Oxygen permeability vs. monomer content \(84\).](#)

[Figure 3.7 Amount of \*Staphylococcus aureus\* on the surface vs. monomer content \(8...](#)

[Figure 3.8 Optical measurement system \(112\).](#)

[Figure 3.9 Swept source optical coherence tomography system \(107\).](#)

## Chapter 4

[Figure 4.1  \$\alpha\$ -Cyclodextrin.](#)

[Figure 4.2 Vitamin E.](#)

[Figure 4.3 Oleic acid.](#)

[Figure 4.4 Cationic drugs.](#)

[Figure 4.5 Unsaturated fatty acids.](#)

[Figure 4.6 Betaxolol hydrochloride.](#)

[Figure 4.7 Chemicals for the synthesis of a HEMA-chitosan polymer.](#)

[Figure 4.8 \*N,N'\*-Carbonyldiimidazole and its methacrylic acid derivative.](#)

[Figure 4.9 Cyclosporine A.](#)

[Figure 4.10 Disodium cromoglycate.](#)

[Figure 4.11 Disuccinimidyl carbonate.](#)

[Figure 4.12 Biotin.](#)

[Figure 4.13 Tobramycin.](#)

[Figure 4.14 Vancomycin.](#)

[Figure 4.15 Amount of drug release vs. time \(64\).](#)

[Figure 4.16 Diazeniumdiolate.](#)

[Figure 4.17 Acetazolamide.](#)

[Figure 4.18 Flurbiprofen.](#)

[Figure 4.19 Timolol.](#)

[Figure 4.20 Change of drug release rate vs. Vitamin E concentration \(107\).](#)

[Figure 4.21 Dexamethasone.](#)

[Figure 4.22 Trisodium citrate.](#)

[Figure 4.23 Ketotifen fumarate.](#)

[Figure 4.24 Ketotifen fumarate in the tear fluid as a function of time \(133\).](#)

[Figure 4.25 Cumulative release of ketotifen fumarate \(95\).](#)

[Figure 4.26 Ciprofloxacin.](#)

[Figure 4.27 3-Methacryloxypropyltris\(trimethylsiloxy\) silane.](#)

[Figure 4.28 Antibacterial ocular drugs.](#)

[Figure 4.29 4-Methyl-4-pentenoic acid.](#)

[Figure 4.30 \*In-vitro\* release as a function of time \(141\).](#)

[Figure 4.31 Polymyxin B.](#)

[Figure 4.32 Vancomycin.](#)

[Figure 4.33 Epinastine.](#)

[Figure 4.34 Bimatoprost.](#)

[Figure 4.35 Dipicolylamine.](#)

[Figure 4.36 Gatifloxacin.](#)

[Figure 4.37 Dorzolamide.](#)

[Figure 4.38 Ethoxzolamide.](#)

[Figure 4.39 Monomers for hydrogels.](#)

[Figure 4.40 \*L\*-Histidine.](#)

[Figure 4.41 Hyaluronic acid.](#)

[Figure 4.42 Compounds used in Preparation 4-4.](#)

[Figure 4.43 Cumulative release of hyaluronic acid \(90\).](#)

[Figure 4.44 Preparation of the ring-implanted contact lenses, reprinted from Mac...](#)

[Figure 4.45 Lifitegrast \(\*N\*-\[\[2-\(6-Benzofuranylcarbonyl\)-5,7-dichloro-1,2,3,4-tet...](#)

[Figure 4.46 Diclofenac sodium.](#)

[Figure 4.47 Release of diclofenac sodium vs. \(M/T\) ratio \(161\).](#)

[Figure 4.48 Cetalkonium chloride.](#)

[Figure 4.49 Moxifloxacin.](#)

[Figure 4.50 \*N\*-\[Tris\(trimethylsiloxy\)silylpropyl\]acrylamide.](#)

[Figure 4.51 Norfloxacin.](#)

[Figure 4.52 Sparfloxacin.](#)

[Figure 4.53 Latanoprost.](#)

[Figure 4.54 Loteprednol etabonate.](#)

[Figure 4.55 Template molecules.](#)

## Chapter 5

[Figure 5.1 Oxamic acid.](#)

[Figure 5.2 Average corneal swelling vs. time \(19\).](#)

[Figure 5.3 Thimerosal.](#)

[Figure 5.4 Poly\(hexamethylene\) biguanide.](#)

[Figure 5.5 Compounds for eye drops.](#)

[Figure 5.6 Denatonium benzoate.](#)

[Figure 5.7 \*N\*-Vinyl-2-pyrrolidone and Vinylimidazolium methochloride.](#)

[Figure 5.8 Saccharides \(46\).](#)

[Figure 5.8 \(cont\) Saccharides \(46\).](#)

[Figure 5.9 Chelating agents.](#)

[Figure 5.10 Preservatives.](#)

[Figure 5.11 Hexamethylene biguanide.](#)

[Figure 5.12 5-Bromo-2'-deoxyuridine.](#)

[Figure 5.13 Hematoxylin.](#)

[Figure 5.14 Compounds for derivatizing.](#)

[Figure 5.15 Diquafosol.](#)

[Figure 5.16 Refractive error change with time \(90, 97\).](#)

## List of Tables

### Chapter 1

[Table 1.1 History of contact lenses \(2\).](#)

[Table 1.2 Monomers for contact lenses.](#)

[Table 1.3 Monomers \(18\).](#)

[Table 1.4 Side-chain-linked amino acids \(18\).](#)

[Table 1.5 Hydrophilic methacrylamide-based monomers \(23\).](#)

[Table 1.6 Hydrophilic polymers \(23\).](#)

[Table 1.7 Multifunctional monomers \(23\).](#)

[Table 1.8 Monomers \(19\).](#)

[Table 1.9 Mechanical properties \(19\).](#)

[Table 1.10 Monomers \(26\).](#)

[Table 1.11 Initiators \(26\).](#)

[Table 1.12 Azlactone monomers \(28\).](#)

[Table 1.13 Monomers for controlling water content \(30\).](#)

[Table 1.14 Nucleating agents \(31\).](#)

[Table 1.15 Crosslinking agents \(39\).](#)

[Table 1.16 Monomers \(43\).](#)

[Table 1.17 Poly\(siloxane\) monomers \(43\).](#)

[Table 1.18 Target biomarkers \(52\).](#)

[Table 1.19 Examples of target analytes \(61\).](#)

[Table 1.20 Common species in tears and blood \(61\).](#)

[Table 1.21 Glucose biosensors developed for contact lenses \(66\).](#)

[Table 1.22 UV-blocking agents \(21\).](#)

[Table 1.23 Silicone monomers \(21\).](#)

[Table 1.24 Composition for a multifocal contact lens \(21\).](#)

[Table 1.25 Monomers for non-silicone hydrogels \(31\).](#)

[Table 1.26 Crosslinking agents for non-silicone hydrogels \(31\).](#)

[Table 1.27 Free radical catalysts and initiators \(31\).](#)

[Table 1.28 Initiators.](#)

[Table 1.29 Contents of the contact lenses \(125\).](#)

[Table 1.30 Free radical generating initiators \(126\).](#)

[Table 1.31 Synthesis and properties of polymers.](#)

[Table 1.32 Monomers \(127\).](#)

[Table 1.33 Isocyanates \(127\).](#)

[Table 1.34 Protein absorption of artificial tear fluid on the surface of sample ...](#)

[Table 1.35 Number of colony-forming units \(141\).](#)

## Chapter 2

[Table 2.1 Optical design software.](#)

[Table 2.2 Inks and pigment levels \(13\).](#)

[Table 2.3 Formulation of contact lens \(25\).](#)

[Table 2.4 Polymers for mat production \(27\).](#)

[Table 2.5 Comonomers for mat production \(27\).](#)

[Table 2.6 Hydrophilic monomers \(31\).](#)

[Table 2.7 Formulation for preparing contact lenses \(40\).](#)

## Chapter 3

[Table 3.1 Standards for testing contact lenses.](#)

[Table 3.2 Potential uses of contact lenses \(44\).](#)

[Table 3.3 Pluronic® surfactants \(55\).](#)

[Table 3.4 Cleaning composition for contact lenses \(55\).](#)

[Table 3.5 Daily disposable lenses \(73\).](#)

[Table 3.6 Roughness values \(91\).](#)

## Chapter 4

[Table 4.1 Setschenow constants.](#)

[Table 4.2 Drugs for molecularly imprinted contact lenses \(68\).](#)

[Table 4.3 monomer mixture for silicone contact lenses \(130, 132\).](#)

[Table 4.4 Formulations of the contact lenses \(95\).](#)

[Table 4.5 Loss of drugs \(132\).](#)

## Chapter 5

[Table 5.1 Eye diseases.](#)

[Table 5.2 Properties of the lenses \(19\).](#)

[Table 5.3 Saccharides \(45\).](#)

[Table 5.4 Chelating agents \(45\).](#)

[Table 5.5 Results of dry-eye study \(89\).](#)



**Scrivener Publishing**

100 Cummings Center, Suite 541J

Beverly, MA 01915-6106

*Publishers at Scrivener*

Martin Scrivener ([martin@scrivenerpublishing.com](mailto:martin@scrivenerpublishing.com))

Phillip Carmical ([pcarmical@scrivenerpublishing.com](mailto:pcarmical@scrivenerpublishing.com))

# Contact Lenses

## Materials, Chemicals, Methods and Applications

**Johannes Karl Fink**

Montanuniversität Leoben, Austria



**WILEY**

This edition first published 2022 by John Wiley & Sons, Inc., 111 River Street, Hoboken, NJ 07030, USA and Scrivener Publishing LLC, 100 Cummings Center, Suite 541J, Beverly, MA 01915, USA

© 2022 Scrivener Publishing LLC

For more information about Scrivener publications please visit [www.scrivenerpublishing.com](http://www.scrivenerpublishing.com).

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system, or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, except as permitted by law. Advice on how to obtain permission to reuse material from this title is available at <http://www.wiley.com/go/permissions>.

### **Wiley Global Headquarters**

111 River Street, Hoboken, NJ 07030, USA

For details of our global editorial offices, customer services, and more information about Wiley products visit us at [www.wiley.com](http://www.wiley.com).

### **Limit of Liability/Disclaimer of Warranty**

While the publisher and authors have used their best efforts in preparing this work, they make no representations or warranties with respect to the accuracy or completeness of the contents of this work and specifically disclaim all warranties, including without limitation any implied warranties of merchantability or fitness for a particular purpose. No warranty may be created or extended by sales representatives, written sales materials, or promotional statements for this work. The fact that an organization, website, or product is referred to in this work as a citation and/or potential source of further information does not mean that the publisher and authors endorse the information or services the organization, website, or product may provide or recommendations it may make. This work is sold with the understanding that the publisher is not engaged in rendering professional services. The advice and strategies contained herein may not be suitable for your situation. You should consult with a specialist where appropriate. Neither the publisher nor authors shall be liable for any loss of profit or any other commercial damages, including but not limited to special, incidental, consequential, or other damages. Further, readers should be aware that websites listed in this work may have changed or disappeared between when this work was written and when it is read.

### ***Library of Congress Cataloging-in-Publication Data***

ISBN 978-1-119-85735-8

Cover image: [Pixabay.com](http://Pixabay.com)

Cover design by Russell Richardson

Set in size of 11pt and Minion Pro by Manila Typesetting Company, Makati, Philippines

Printed in the USA

10 9 8 7 6 5 4 3 2 1

# Preface

This book focuses on the chemistry and properties of contact lenses and their fabrication methods.

The text starts with a chapter in which a detailed history of contact lenses spanning over almost 500 years is presented

Next, common materials that are used for the fabrication of contact lenses are listed and explained, including both the monomers and polymers that are used in their production. Special issues regarding soft lenses, clear contact lenses, and functional contact lenses are also discussed.

Functional contact lenses can be used for remote health monitoring and ocular drug delivery systems. Besides the materials used here, these issues are detailed in further separate chapters. Also, special fabrication methods are discussed, e.g., the fabrication of multifocal contact lenses and the fabrication of ultrathin coatings.

There is also an important discussion on additives that can be used, e.g., for oxygen-permeable materials or anti-biofouling materials.

The chapter ends with a discussion of simulation methods for contact lenses, such as ocular topography parameters, gas-permeable lenses, and computerized videokeratography.

In the second chapter, several common fabrication methods for contact lenses are discussed. Here, computer-aided contact lens design, methods for the fabrication of colored contact lenses, and the fabrication of decentered contact lenses are detailed.

Also, special processes are reviewed, including mold processes, reactive ion etching, electrospinning and others.

Another chapter discusses the properties of contact lenses and methods of measurement. Here, a lot of standard methods are discussed. Besides standard methods, other issues are discussed such as the assessment of cytotoxic effects, the Schirmer tear test and others.

A chapter is devoted to drug delivery of contact lenses, a comparatively new issue.

Finally, a chapter details the possible medical problems related to contact lenses and how to avoid them. These are eye diseases, allergic and toxic reactions. Also, disinfection agents that can be used and methods for the medical treatment of such problems are detailed.

The text focuses on the literature of the past decade. Beyond education, this book will serve the needs of industry engineers and specialists who have only a passing knowledge of the plastics and composites industries but need to know more.

### ***How to Use This Book***

Utmost care has been taken to present reliable data. Because of the vast variety of material presented here, however, the text cannot be complete in all aspects, and it is recommended that the reader study the original literature for more complete information.

The reader should be aware that mostly US patents have been cited where available, but not the corresponding equivalent patents in other countries. For this reason, the author cannot assume responsibility for the completeness, validity or consequences of the use of the material presented herein. Every attempt has been made to identify trademarks; however, there were some that the author was unable to locate.

### ***Index***

There are three indices: an index of acronyms, an index of chemicals, and a general index.

In the index of chemicals, compounds that occur extensively, e.g., “acetone,” are not included at every occurrence, but rather when they appear in an important context.

## **Acknowledgements**

I am indebted to our university librarians, Dr. Christian Hasenhüttl, Margit Keshmiri, Friedrich Scheer, Christian Slamenik, Renate Tschabuschnig, and Elisabeth Groß for their support in literature acquisition. I also want to express my gratitude to all the scientists who have carefully published their results concerning the topics dealt with herein. This book could not have been otherwise compiled.

In addition, I am very grateful to the ophthalmologists Dr. Anna Schlanitz-Bolldorf and Dr. Ferdinand Schlanitz, who inspired me to write this text. Last, but not least, I want to thank the publisher, Martin Scrivener, for his abiding interest and help in the preparation of the text. In addition, my thanks go to Jean Markovic, who made the final copyedit with utmost care.

**Johannes Fink**  
Leoben, December 2, 2021

# 1

## Types of Lenses

### 1.1 History of Contact Lenses

A history of contact lenses spanning over almost 500 years has been detailed (1, 2). It is based on historical works, scientific papers and journal articles and looks at both the modern disposable lens as well as the hard and soft lenses that came before. Some important events are collected in [Table 1.1](#).

**Table 1.1** History of contact lenses (2).

Year	Inventor	Issue
1508	Leonardo da Vinci	Corneal neutralization
1637	René Descartes	Fluid-filled tube
1685	Philippe de La Hire	Neutralization of cornea
1801	Thomas Young	Three color theory of perception
1827	George Biddell	Theory of astigmatism
1845	Sir John F. W. Herschel	Convex lenses
1846	Carl Zeiss	Optical instruments
1851	Johann Nepomuk Czermak	Water-filled goggle
1887	Adolf Eugen Fick	First successful contact lens
1961	Otto Wichterle	Soft contact lenses
1979	Kyoichi Tanaka	Silicone hydrogel materials

In 1508, Leonardo da Vinci first had the idea of placing a corrective lens directly onto the surface of the eye (3-5). In 1637, René Descartes proposed another idea in which a glass tube filled with liquid is placed in direct contact with the cornea.

In 1887, Adolf Eugen Fick, a German physiologist, created the first successful contact lens (6). Glass-blown scleral lenses remained the only form of contact lens until 1938, when poly(methyl methacrylate) (PMMA) was developed, and Mullen and Obring used the plastic to manufacture scleral lenses. Obring developed the Plexiglass series in New York in 1940 (4).



In 1961, the Czech chemist Otto Wichterle invented soft contact lenses (7, 8). In 1970, rigid gas-permeable contact lenses were developed, and widely accepted for the advantages of small diameter (about 9 *mm*) and gas permeability. Silicone hydrogel materials were developed in 1979 (9). In 1999, an important development was the launch of the first silicone hydrogels onto the market. These new materials showed an extremely high oxygen permeability with comfort performance (4).

The factors that influenced the development of special materials have been reported (10). Accounts of early attempts to improve vision by use of a lens contacting the eye are limited to a few isolated observations (11). Practical success was not realized until techniques for fabrication of lenses from glass were sufficiently developed (12). PMMA replaced glass in the late 1930s. This material is more durable, more readily fabricated and was claimed by some authors to show a better ocular compatibility (13). During the same broad period of time, there was also a change in emphasis from scleral to corneal contact lenses, which placed different demands on material design and development.

More is demanded from ophthalmic treatments using contact lenses, which are currently used by over 125 million people around the world (14). Improving the material of contact lenses is currently a rapidly evolving discipline (10).

A search has been performed of the titles of papers in the Scopus database to identify contact lens-related articles published this century (15). The ten most highly cited papers were determined from the total list of 4,164 papers found. Rank-order lists by count were assembled for the *top 25* in each of four categories: authors, institutions, countries and journals. A 20-year subject-specific contact lens h-index was derived for each author, institution, country and journal to serve as a measure of impact in the field. The top 10 constituents (of the top 25) of each category were ranked and tabulated (15).

## **1.2 Materials**

Contact lens materials (10) are typically based on polymer- or silicone-hydrogel, with additional manufacturing technologies employed to produce the final lens. These processes are simply not enough to meet the increasing demands for contact lenses and the ever-increasing number of contact lens users (14).

An advanced perspective on contact lens materials has been presented, with an emphasis on materials science employed in developing new contact lenses (14, 16). The future trends for contact lens materials are

to graft, incapsulate, or modify the classic contact lens material structure to provide new or improved functionality. Also, some of the fundamental material properties are discussed, and the outlook for related emerging biomaterials is presented.

Contact lens materials and lens types, treatment for contact lens and tear film complications, and myopia correction and contact lenses for abnormal ocular conditions have been detailed (17). Current topics in this field are miniscleral lenses, keratoconus, corneal crosslinking, and pediatric, cosmetic and prosthetic contact lenses. Furthermore, simulation programs for scleral lens fitting, sagittal values, soft toric mislocation, front vertex power, orthokeratology and rigid lens design are discussed.

## **1.3 Monomers**

The monomers that can be used for contact lenses, which are described in the following sections and in both tables and references, are collected in [Table 1.2](#).

These issues will be detailed in the following sections of this chapter.

### ***1.3.1 Monomers for Block Copolymers***

A block copolymer that contains both hydrophobic and hydrophilic blocks with amino acid groups has been described (18).

The principal monomers for such block copolymers are a combination of two monomers capable of forming a hydrogel; such monomers are collected in [Table 1.3](#).

**Table 1.2** Monomers for contact lenses.

Monomers and monomer types	Usage	References
2-Hydroxyethyl methacrylate <i>N</i> -Vinyl-2-pyrrolidone Methyl methacrylate Isobornyl methacrylate <i>tert</i> -Butylcyclohexyl methacrylate	Soft lenses	(19)
Hydrophobic monomers	Strengthening agents	<a href="#">Table 1.8</a>
Hydrophilic monomers		<a href="#">Table 1.8</a>
Hydrophilic monomers	Hydrogels	<a href="#">Table 1.10</a>
Azlactones	Surface treatment	<a href="#">Table 1.12</a>
Acrylamide <i>N</i> -Hydroxyethyl acrylamide <i>N</i> -Isopropyl acrylamide 2-Acrylamido-2-methylpropane-sulfonic acid 2-Hydroxyethyl methacrylate 2-Hydroxyethyl acrylate	Macromers	(20)
Acryl monomers	Water absorbable	<a href="#">Table 1.16</a>
Poly(siloxane)	Water absorbable	<a href="#">Table 1.17</a>
4-(Phenyldiazenyl) phenyl methacrylate	Blue-light blocking	(21)
Acrylates	UV-blocking	<a href="#">Table 1.22</a>
Silicone hydrogel	Multifocal lenses	<a href="#">Table 1.23</a>
Acrylates	Non-silicone hydrogel	<a href="#">Table 1.25</a>
Crosslinking agents	Non-silicone hydrogel	Table <a href="#">Table 1.26</a>
Oxyperm	Oxygen permeable	<a href="#">Table 1.32</a>
Ionoperm	Oxygen permeable	<a href="#">Table 1.32</a>

**Table 1.3** Monomers (18).

Monomer	Monomer
2-Ethylphenoxy acrylate	2-Ethylphenoxy methacrylate
2-Ethylthiophenyl acrylate	2-Ethylthiophenyl methacrylate
2-Ethylaminophenyl acrylate	2-Ethylaminophenyl methacrylate
Phenyl acrylate	Phenyl methacrylate
Benzyl acrylate	Benzyl methacrylate
2-Phenylethyl acrylate	2-Phenylethyl methacrylate
3-Phenylpropyl acrylate	3-Phenylpropyl methacrylate
3-Propylphenoxy acrylate	3-Propylphenoxy methacrylate
4-Butylphenoxy acrylate	4-Butylphenoxy methacrylate
4-Phenylbutyl acrylate	4-Phenylbutyl methacrylate


Side-chain-linked amino acids are collected in [Table 1.4](#). Some of these compounds are shown in [Figure 1.1](#).

**Table 1.4** Side-chain-linked amino acids (18).


Monomer	Monomer
Acryloyl- <i>L</i> -lysine	Acryloyl- <i>L</i> -serine
Acryloyl- <i>L</i> -threonine	Acryloyl- <i>L</i> -tyrosine
Acryloyl- <i>L</i> -amino-phenylalanine	Acryloyl- <i>L</i> -cysteine
Acryloyl- <i>L</i> -oxy-proline	N $\epsilon$ -acryloyl-N $\alpha$ -Oelityl- <i>L</i> -Lysine

The synthesis of a variety of such monomers has been detailed (18). For example, the synthesis of (*S*)-6-acrylamido-2-aminohexanoic acid monomers is performed via a copper complex (18):


**Preparation 1-1:** L-lysine (14.62 g; 100 mmol) was dissolved in 150 ml deionized water and heated to about 80°C. Copper carbonate (16.6 g; 75 mmol) was added in portions over a period of 30 min. The reaction was stirred for an additional 30 min. The hot, deep-blue suspension was filtered through silica gel. The filter was washed with a small amount of water. On the following day, the lysine copper complex containing the combined filtrate was cooled in an ice bath, and 100 ml tetrahydrofuran was added. A solution of acryloyl chloride in methyl-*tert*-butylether (8.9 ml, 110 mmol) was added dropwise during a period of 1 h. The pH was initially maintained between 8 and 10 by parallel, dropwise addition of 10% sodium hydroxide solution. After half of the acryloyl chloride solution had been added, the product began to precipitate. When most of the acryloyl chloride had been added, addition of sodium hydroxide was slowed down to allow the pH to drop to about 6 and the temperature of the reaction mixture was allowed to reach room temperature. The blue suspension was stirred for an additional 2 h and was then filtered. The solid material retained on the filter was washed with water and acetone and then dried. A yield of 6.5 g of acryloyl-*L*-lysine copper complex was obtained. Acryloyl-*L*-lysine copper complex (29.5 g) was suspended in 300 ml deionized water and cooled in an ice bath. H<sub>2</sub>S gas was bubbled into the suspension until copper sulfide precipitation was complete; then 3 g of active charcoal was added to the suspension. The suspension was heated briefly to 100°C. After cooling to room temperature, 500 ml acetone was added to the suspension which was then filtered on silica gel. The clear filtrate was put in a rotary evaporator. After evaporation of the solvent, the solid product was recrystallized from 200 ml of 50% aqueous acetone. A yield of 17.76 g (69.76%) of white powder was obtained. The structure of the compound was verified by nuclear magnetic resonance spectroscopy and LC-MS spectroscopy.

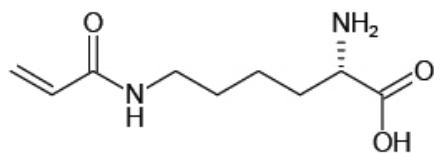


Acryloyl-*L*-lysine

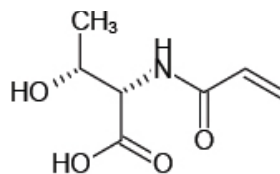

Acryloyl-*L*-threonine

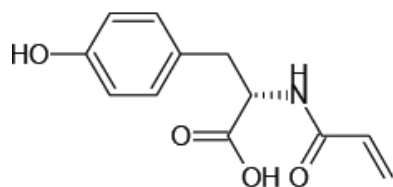

Acryloyl-*L*-tyrosine

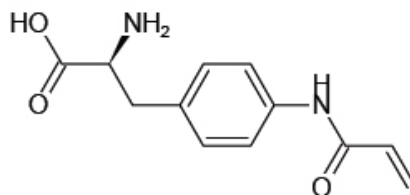

Acryloyl-*L*-amino-phenylalanine

**Figure 1.1** Monomers for side-chain-linked amino acids.

The preparation of a block copolymer containing a hydrophilic cellophil polymer and a lipid-like copolymer was done by raft polymerization as follows (18):