

Jörg Friedrich

 WILEY-VCH

The Plasma Chemistry of Polymer Surfaces

Advanced Techniques for Surface Design

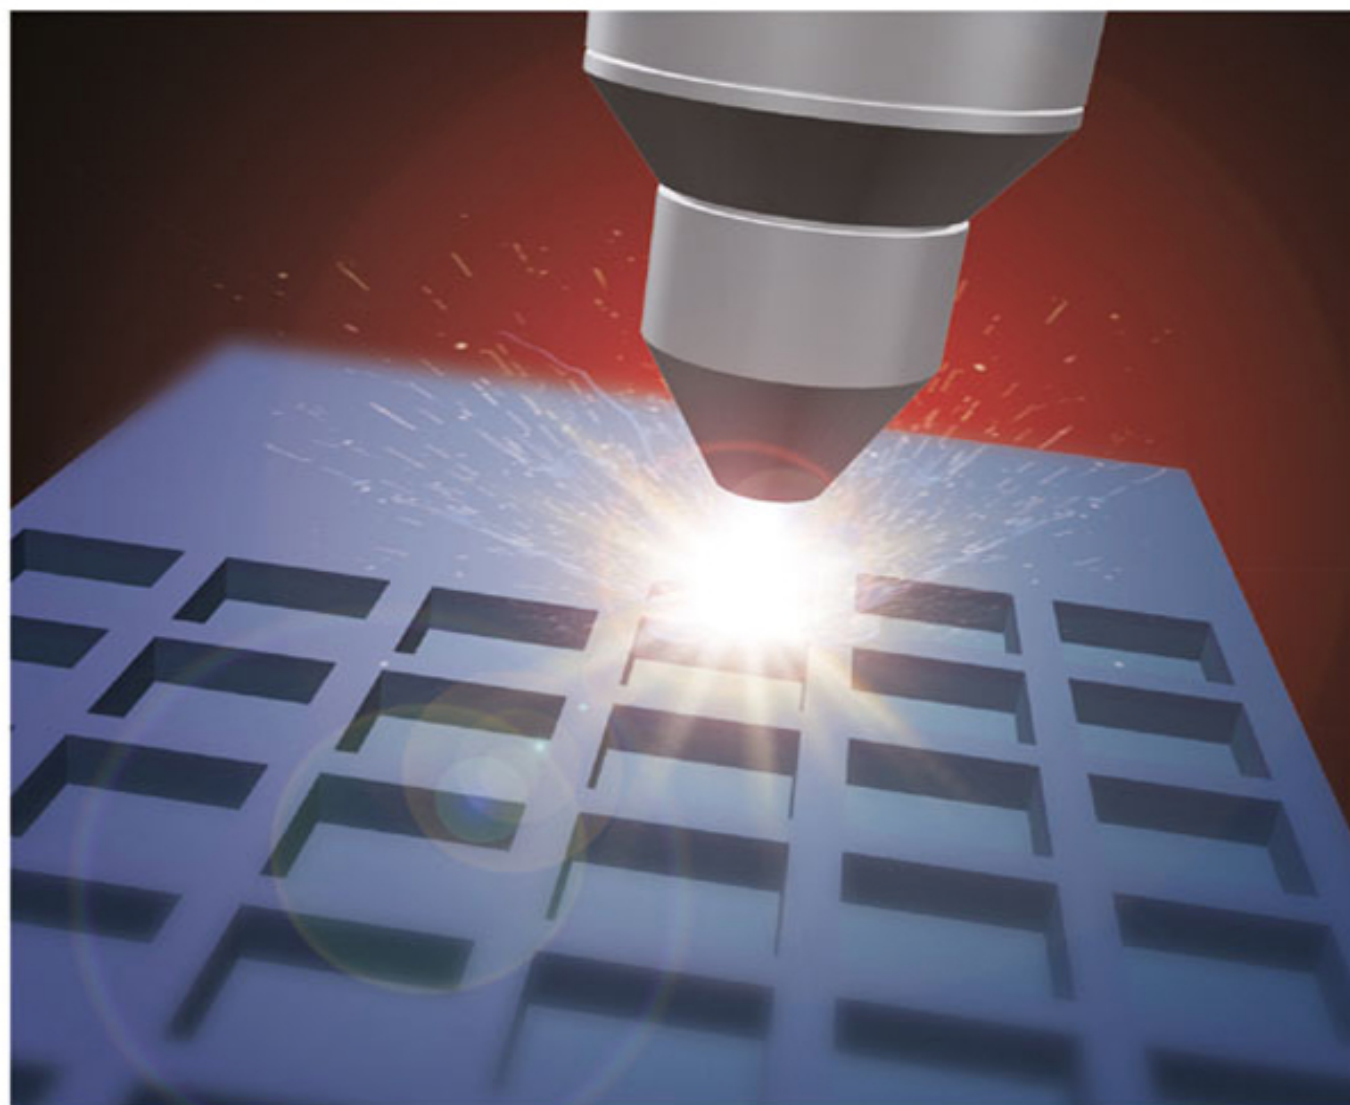


Table of Contents

Cover

Related Titles

Title page

Copyright page

Preface

1 Introduction

2 Interaction between Plasma and Polymers

2.1 Special Features of Polymers

2.2 Processes on Polymer Surfaces during Plasma Exposure

2.3 Influence of Polymer Type

2.4 Methods, Systematic, and Definitions

2.5 Functional Groups and Their Interaction with Other Solids

3 Plasma

3.1 Plasma State

3.2 Types of Low-Pressure Glow Discharges

3.3 Advantages and Disadvantages of Plasma Modification of Polymer Surfaces

3.4 Energetic Situation in Low-Pressure Plasmas

3.5 Atmospheric and Thermal Plasmas for Polymer Processing

3.6 Polymer Characteristics

3.7 Chemically Active Species and Radiation

4 Chemistry and Energetics in Classic and Plasma Processes

4.1 Introduction of Plasma Species onto Polymer Surfaces

4.2 Oxidation by Plasma Fluorination and by Chemical Fluorination

4.3 Comparison of Plasma Exposure, Ionizing Irradiation, and Photo-oxidation of Polymers

5 Kinetics of Polymer Surface Modification

5.1 Polymer Surface Functionalization

5.2 Polymer Surface Oxidation

5.3 Polymer Surface Functionalization with Amino Groups

5.4 Carbon Dioxide Plasmas

5.5 SH-Forming Plasmas

5.6 Fluorinating Plasmas

5.7 Chlorination

5.8 Polymer Modification by Noble Gas Plasmas

6 Bulk, Ablative, and Side Reactions

6.1 Changes in Supramolecular Structure of Polymers

6.2 Polymer Etching

6.3 Changes in Surface Topology

6.4 Plasma Susceptibility of Polymer Building Blocks

6.5 Plasma UV Irradiation

6.6 Absorption of Radiation by Polymers

6.7 Formation of Unsaturation

6.8 Formation of Macrocycles

6.9 Polymer Degradation and Supramolecular Structure of Polymers

6.10 Crosslinking versus Degradation of Molar Masses

6.11 Radicals and Auto-oxidation

6.12 Plasma-Induced Photo-oxidations of Polymers

6.13 Different Degradation Behavior of Polymers on Exposure to Oxygen Plasma

6.14 Derivatization of Functional Groups for XPS

7 Metallization of Plasma-Modified Polymers

7.1 Background

7.2 Polymer Plasma Pretreatment for Well Adherent Metal-Polymer Composites

7.3 New Adhesion Concept

7.4 Redox Reactions along the Interface

7.5 Influence of Metal-Polymer Interactions on Interface-Neighbored Polymer Interphases

7.6 Metal-Containing Plasma Polymers

7.7 Plasma-Initiated Deposition of Metal Layers

7.8 Inspection of Peeled Surfaces

7.9 Life Time of Plasma Activation

8 Accelerated Plasma-Aging of Polymers

8.1 Polymer Response to Long-Time Exposure to Plasmas

8.2 Hydrogen Plasma Exposure

8.3 Noble Gas Plasma Exposure, CASING

9 Polymer Surface Modifications with Monosort Functional Groups

9.1 Various Ways of Producing Monosort Functional Groups at Polyolefin Surfaces

9.2 Oxygen Plasma Exposure and Post-Plasma Chemical Treatment for Producing OH Groups

9.3 Post-Plasma Chemical Grafting of Molecules, Oligomers, or Polymers

9.4 Selective Plasma Bromination for Introduction of Monosort C-Br Bonds to Polyolefin Surfaces

9.5 Functionalization of Graphitic Surfaces

9.6 SiO_x Deposition

9.7 Grafting onto Radical Sites

10 Atmospheric-Pressure Plasmas

10.1 General

10.2 Dielectric Barrier Discharge (DBD) Treatment

10.3 Polymerization by Introduction of Gases, Vapors, or Aerosols into a DBD

10.4 Introduction of Polymer Molecules into the Atmospheric-Pressure Plasma and Their Deposition as Thin Polymer Films (Aerosol-DBD)

10.5 DBD Treatment of Polyolefin Surfaces for Improving Adhesion in Metal-Polymer Composites

10.6 Electrospray Ionization (ESI) Technique

11 Plasma Polymerization

11.1 Historical

11.2 General Intention and Applications

11.3 Mechanism of Plasma Polymerization

11.4 Plasma Polymerization in Adsorption Layer or Gas Phase

11.5 Side-Reactions

11.6 Quasi-hydrogen Plasma

11.7 Kinetic Models Based on Ionic Mechanism

11.8 Kinetic Models of Plasma-Polymer Layer Deposition Based on a Radical

Mechanism

11.9 Dependence on Plasma Parameter

11.10 Structure of Plasma Polymers

11.11 Afterglow (Remote or Downstream)

Plasmas

11.12 Powder Formation

11.13 Plasma Catalysis

11.14 Copolymerization in Continuous-Wave Plasma Mode

12 Pulsed-Plasma Polymerization

12.1 Introduction

12.2 Basics

12.3 Presented Work on Pulsed-Plasma Polymerization

12.4 Role of Monomers in Pulsed-Plasma Polymerization

12.5 Dark Reactions

12.6 Pressure-Pulsed Plasma

12.7 Differences between Radical and Pulsed-Plasma Polymerization

12.8 Surface Structure and Composition of Pulsed-Plasma Polymers

12.9 Plasma-Polymer Aging and Elimination of Radicals in Plasma Polymers

12.10 Functional Groups Carrying Plasma-Polymer Layers

12.11 Vacuum Ultraviolet (VUV) Induced Polymerization

12.12 Plasma-Initiated Copolymerization

12.13 Graft Polymerization

12.14 Grafting onto Functional Groups

Index

Related Titles

Parvulescu, V. I., Magureanu, M., Lukes, P. (eds.)

Plasma Chemistry and Catalysis in Gases and Liquids

2012

ISBN: 978-3-527-33006-5

Schlüter, D. A., Hawker, C., Sakamoto, J. (eds.)

Synthesis of Polymers

New Structures and Methods

Series: Materials Science and Technology

2 Volume Set

2012

ISBN: 978-3-527-32757-7

Knoll, W. Advincula, R. C. (eds.)

Functional Polymer Films

2 Volume Set

2011

ISBN: 978-3-527-32190-2

Harry, J. E.

Introduction to Plasma Technology

Science, Engineering and Applications

2010

ISBN: 978-3-527-32763-8

Kawai, Y., Ikegami, H., Sato, N., Matsuda, A., Uchino, K., Kuzuya, M., Mizuno, A. (eds.)

Industrial Plasma Technology

Applications from Environmental to Energy Technologies

2010

ISBN: 978-3-527-32544-3

Rauscher, H., Perucca, M., Buyle, G. (eds.)

Plasma Technology for Hyperfunctional Surfaces

Food, Biomedical, and Textile Applications

2010

ISBN: 978-3-527-32654-9

Hippler, R., Kersten, H., Schmidt, M., Schoenbach, K. H.
(eds.)

Low Temperature Plasmas

Fundamentals, Technologies and Techniques

2nd, revised and enlarged edition

2008

ISBN: 978-3-527-40673-9

Ostrikov, K.

Plasma Nanoscience

**Basic Concepts and Applications of Deterministic
Nanofabrication**

2008

ISBN: 978-3-527-40740-8

Coqueret, X., Defoort, B. (eds.)

High Energy Crosslinking Polymerization

Applications of Ionizing Radiation

2006

ISBN: 978-3-527-31838-4

Lazzari, M., Liu, G., Lecommandoux, S. (eds.)

Block Copolymers in Nanoscience

2006

ISBN: 978-3-527-31309-9

Jörg Friedrich

The Plasma Chemistry of Polymer Surfaces

Advanced Techniques for Surface Design



WILEY-VCH Verlag GmbH & Co. KGaA

The Author

Prof. Dr. Jörg Friedrich

BAM – Bundesanstalt für
Material forschung u. -prüfung
Unter den Eichen 87
12205 Berlin

All books published by **Wiley-VCH** are carefully produced. Nevertheless, authors, editors, and publisher do not warrant the information contained in these books, including this book, to be free of errors. Readers are advised to keep in mind that statements, data, illustrations, procedural details or other items may inadvertently be inaccurate.

Library of Congress Card No.: applied for

British Library Cataloguing-in-Publication Data

A catalogue record for this book is available from the British Library.

Bibliographic information published by the Deutsche Nationalbibliothek

The Deutsche Nationalbibliothek lists this publication in the Deutsche Nationalbibliografie; detailed bibliographic data are available on the Internet at <<http://dnb.d-nb.de>>.

© 2012 Wiley-VCH Verlag & Co. KGaA, Boschstr. 12, 69469 Weinheim, Germany

All rights reserved (including those of translation into other languages). No part of this book may be reproduced in any form – by photoprinting, microfilm, or any other means – nor transmitted or translated into a machine language without written permission from the publishers. Registered names, trademarks, etc. used in this book, even when not specifically marked as such, are not to be considered unprotected by law.

Print ISBN: 978-3-527-31853-7
ePDF ISBN: 978-3-527-64803-0
oBook ISBN: 978-3-527-64800-9
ePub ISBN: 978-3-527-64802-3
mobi ISBN: 978-3-527-64801-6

Preface

Some 40 years experience with plasmas applied to polymers and the special view of a polymer chemist are the motivation for writing this book. The rapid growth of applications of plasma processes on an industrial scale is connected with the pioneering work of engineers. Basic research into plasmas and their properties is associated with plasma and astrophysics. Pure plasmas of noble gases under well-defined conditions in exactly determined geometries are traditional objects of plasma physics. Thus, chemical processes are out of view. However, in such simple systems the chemistry of irradiation and release of degradation products also play an important role, as do the polymer surface, near-surface layers, plasma boundary layer, and plasma bulk. Organic and polymer chemistry often dominate the use of molecular plasmas for polymer surface treatment and modification. A much more complicated and complex situation is found for plasma polymerization processes, which can often be described only by formal kinetics as the elementary and chemical processes are not known in exact detail. Electrical low- and atmospheric-pressure plasmas are characterized by a surplus in energy and enthalpy needed for simple chemical processes. The chemistry of excess energy allows endothermic reactions to be performed because the dose rate exceeds all necessary enthalpies of reaction pathways known in chemistry or even in radiation chemistry. Thus, random, statistic, and exotic processes dominate and, therefore, the reaction products are most often chemically irregular in terms of structure and composition. Additionally, the polymer products are unstable because of plasma-produced metastable radicals that are trapped in the polymer bulk and which subsequently remain capable of undergoing oxidation on exposure to oxygen from air. Therefore, the plasma product is unstable and changes

continuously during storage. A nice example may illustrate such a “terrible” plasma. At the beginning of my work, in the early 1970s, I had scraped plasma polymers from the wall of the plasma reactor for infrared analysis. The plasma polymer flakes were collected, cooled with liquid nitrogen, and then ground for production of polymer powder. This powder was disseminated in KBr powder, which is necessary for KBr disk preparation. After evaporation of nitrogen the sample began to smolder and became black. The technical assistant was stunned and did not want to continue his work with other samples. The behavior of the sample was, in fact, due to the fast reaction of radicals that came into contact with oxygen from the air after the plasma polymer layer was disintegrated. Peroxide formation and undefined auto-oxidation were initiated.

Organic chemists or polymer chemists turn away from such “black box chemistry,” labeling it as impure chemistry, far from regular chemistry, that does not follow a defined chemical mechanism. Thus, the pure chemist is shocked and all his knowledge is superfluous. If a polymer chemist must accept that chemically inert gases, such as methane or benzene, can be polymerized or polymers exposed to plasmas are destroyed, degraded, etched, and so on, any previous thinking, any knowledge, is of no help.

The task of this book is to bring together physicists, engineers, chemists, and polymer researchers, looking preferentially from the chemical and especially from the polymer chemical point of view into plasma processes and the reactions in the polymer body. Here, a new type of plasma chemist, who treats and produces polymers, is created or, better, a plasma polymer chemist is born.

Forty years of experience with plasma and polymer chemistry, analysis, and polymer degradation have been concentrated in this book. It discusses important findings in this field from all parts of the world.

Jörg Friedrich

Berlin, 20th September 2011

1

Introduction

The interaction of polymers with different materials such as metals, ceramics, other polymers, coatings, or inorganics is crucial for the adhesion at interfaces in polymer composite structural elements. The absence or weakness of interactions as well as any lack of durability are responsible for the collapse of load-bearing composite components. In 2005 the ice rink in Bad Reichenhall (Germany) collapsed, burying several people, because of adhesion failure (fatigue of the interface bonds).

Many polymers, in particular polyolefins, such as polyethylene and polypropylene are chemically inert and cannot strongly interact with other materials. The reason for this is the absence of polar and reactive functional groups in their structure. Thus, interactions with other materials are poor and so too is adhesion. Weak physical interactions only occur. J. D. van der Waals found their existence in 1879 [1]. These forces are electrostatic, induced and permanent dipoles, dispersion interactions, and hydrogen bonds. They are very weak and operate over a short range [2]. Polyolefins show only dispersion interactions among their own molecules and, thus, they are often difficult to wet or bond because of the absence of polar groups, which are able to promote interactions to the other material. Dipole or induced-dipole interactions or even chemical bonds between polymer and coating at the interface require the existence of functional groups.

Polar groups are often introduced by flaming [3] or plasma exposure [4]. Such oxidations form various oxidized polar

species at the polyolefin surface, which can undergo the desired interactions to other materials. The introduction of chemical bonds at the interface is more efficient because of the much higher binding energies [5]. To install such covalent bonds between polymers and coatings, most often the production of monotype functional groups at the polyolefin surface is a necessary precondition. Such monosort functionalization is extraordinarily difficult. New processes have been developed for its realization, that is, exposure of the polyolefin surface to brominating plasma [6]. The C-Br groups could be converted into amino, carboxyl, or hydroxyl groups or consumed by amines, alcohols, and glycols [7]. The additional introduction of flexible, water-repellent, and metal-binding spacer molecules by grafting onto C-Br groups produced highly adhered and durable polyolefin composites [8].

In highly stressed polymer components for structural assemblies all forces are applied to the interface and distributed to the interfacial bonds. Either a large number of weak physical interactions or a smaller number of strong chemical bonds is needed to withstand the disruption under mechanical load along the interface. However, in general, chemically and structurally, completely different materials need to be joined together. Polymers, in particular polyolefins, show very low surface energy and metals or inorganics a much higher one. The difference amounts to two orders of magnitude (original value for polymers 30-40 mN m^{-1} and for metals 1000-3000 mN m^{-1}), which is nearly the same difference in surface energy as before polymer treatment (40-50 and 1000-3000 mN m^{-1}) [9]. At the molecular level, interactions are absent due to the chemical inertness of polyolefins.

Post-polymerization introduction of functional groups onto polyolefin surfaces has a principal problem. The (radical) substitution of H by any functional group is accompanied by

C-C bond scissions of the polymer backbone because of equivalent (or lower) binding energies [10]. Thus, degradation occurs simultaneously, although C-C bonds were partially shielded from attack. Nevertheless, such a disruption of the polymer surface produces anchoring points for physical and chemical interactions but also a weak boundary layer, which is mechanically, chemically, and thermally unstable (low molecular weight oxidized material, LMWOM) [11]. Moreover, polymers, metals, or inorganics have thermal expansion coefficients that differ by two orders of magnitude. Therefore, the thus produced mechanical stress is focused onto the monolayer of interactions along the interface. As mentioned before, spacer introduction can balance this mechanical stress along the interface.

The surface modification of polyolefins must be also considered within the framework of 100 Mio tons production of polyethylene and polypropylene per year worldwide. Several technical applications demand a solution to the adhesion problem. Mechanical interlocking, chemical roughening by etching, ion and electron beam modification, UV irradiation, UV-induced graft copolymerization, laser beam or excimer lamp irradiation, ^{60}Co irradiation, flaming, corona treatment, use of adhesion promoters, glues, adhesives, etc. were successfully tested to modify polyolefin surfaces for adhesion [2]. However, all these pretreatments produce a broad variety of different functional groups.

As mentioned before, the formation of monotype functional groups followed by spacer grafting can solve the problem of moderate adhesive bond strength and durability. However, the great energy and enthalpy excess present in a plasma is most often responsible for non-selective reactions and the formation of a broad variety of products [12].


The dream of all plasma chemists is to achieve monosort functionalized polyolefin surfaces. The excess energy

present in the plasma state [13] and the equivalency of C-C and C-H dissociation energies make it difficult to realize this dream [10]. However, a few chemical reactions produce end-products that are also stable towards plasma. Examples of such stable end-products are (i) in the case of bromination the electronic state of the neighboring noble gas (krypton) and (ii) silica-like SiO_x layers formed in the oxidation of Si compounds in an oxygen plasma [14].

This book presents several variants of such surface techniques with monotype functional groups, such as chemical post-plasma reduction, pulse-pressure plasma polymerization, underwater plasma and glow discharge electrolysis, and deposition of functionalized prepolymers and oligomers by aerosol plasma and electrospray [15].

Polyolefins have a semi-crystalline structure, which can be represented by the model of “Fransenmicelle” as shown in Figure 1.1.

Figure 1.1 Assumed structure of polyethylene at the surface without functional groups (a), and after surface oxidation and introduction of oxygen-containing functional groups groups (b) and the behavior after wetting with a drop of water.

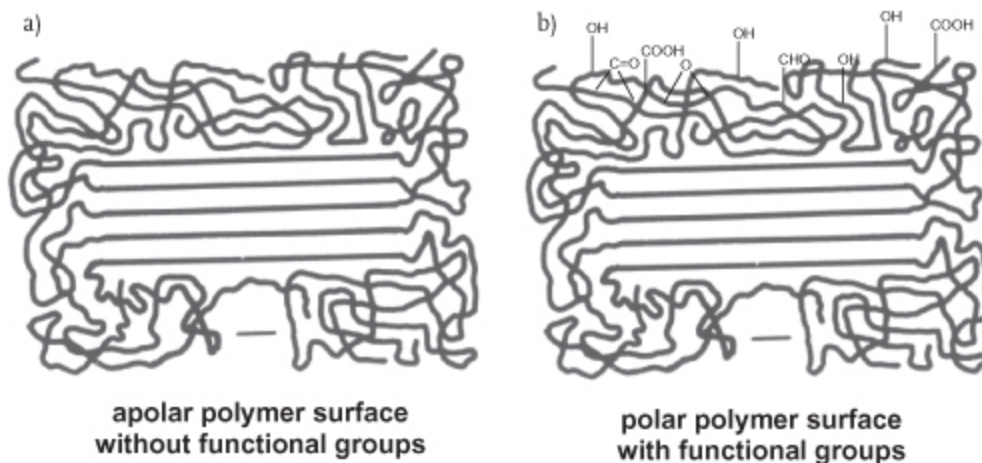


Amorphous regions are characterized by random localization of macromolecular chains, whereas crystalline

regions show the parallel and close orientation of the all-trans configuration of the chain with folded loops, thus forming the lamellae as present in polyethylene [16].

The concept of polymer functionalization by plasma exposure is to attach atoms or fragments of the dissociated plasma gas as functional group by H substitution at the polymer chain. Since there are there many different fragments and atoms present in the plasma a broad variety of related functional groups is produced. The formation of at least 12 oxygen-containing groups at the surface of poly(ethylene terephthalate) has been shown after oxygen plasma exposure [17].

There is also an interrelation between plasma, polymer, surface charging, surface cleaning, surface functionalization, etching, and emission of degradation products as well as changing of plasma by the appearance of oxygen-containing groups in the gas phase and so on (Figure 1.2).


Figure 1.2 Changes in plasma phase upon polymer etching.

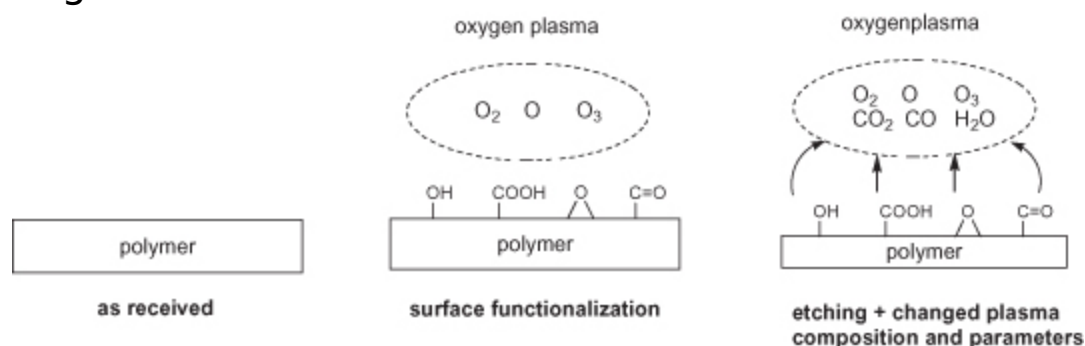

The substrate, here the polymer, gives a specific response to plasma exposure. Polymers react very sensitively to any exposure to plasmas. This is due to their complex and supermolecular structure. Polymers have some common features with living matter and therefore they are very sensitive, in almost the same manner, towards particle or radiation exposure. Thus, special knowledge of polymer


chemistry, physics, and technology is necessary to understand the specific and complex behavior of polymer surfaces on plasma exposure. Starting from plasma physics and taking simple atomic (noble) or molecule gas plasmas, which are well-defined and well-characterized but, nevertheless, are associated with high power consumption and high average electron energy the contradictoriness of flow from plasma to polymer, thus the confrontation is perfect. A shower of high-energy particles and photons bombards the polymer surface. A result of this bombardment is the formation of degraded or crosslinked products with the complete loss of original structure (Figure 1.3) [18].

Figure 1.3 Plasma particle shower and vacuum UV (VUV) irradiation of polymer surfaces during plasma exposure.

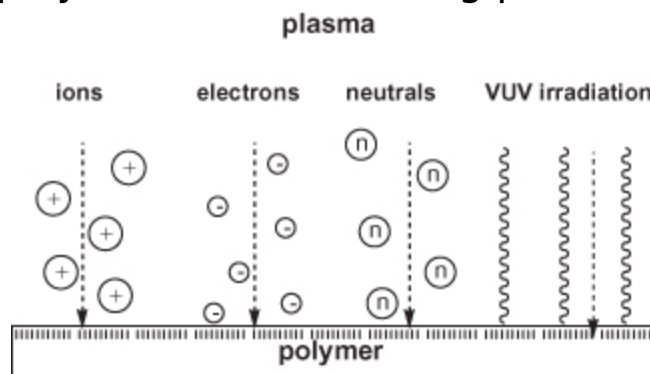


As a matter of course, as a precondition, the plasma gas temperatures should be near room temperature or, in the case of energy-rich hot plasmas, a very short residence time in the plasma zone is mandatory. Low gas temperature is characteristic for low-pressure glow discharges, also known as non-isothermal plasmas or colloquially as "cold" plasmas [19]. Figure 1.4 shows schematically the prototype of such a plasma, namely, the low-pressure DC (direct current) glow discharge. The volume between the two electrodes is filled with the uniform plasma of the "positive column," which is the most suitable place for polymer treatment.

Figure 1.4 Principle of plasma formation: direct current (DC) discharge tube with electrons, ions, and energy-rich neutrals as excited states.

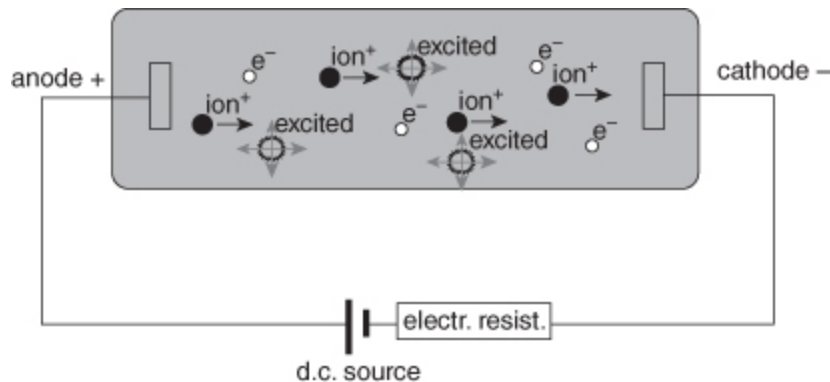

This type of discharge is very seldom used today because of the permanent danger of electrode contamination and coating, which influence the plasma characteristics. Capacitively or inductively coupled radio-frequency (rf) or microwave (mw) generated plasmas are used more often. Figure 1.5 shows the often used diode-like reactor type, which is the most important among the broad variety of plasmatron constructions. It is an example for the production of low-pressure plasmas, called diode-like or parallel-plate reactor. Normally, one electrode is mass (asymmetric coupling).

Figure 1.5 Example of a plasma reactor: a diode-like plasmatron that produces a low-pressure plasma suitable for polymer surface modification.

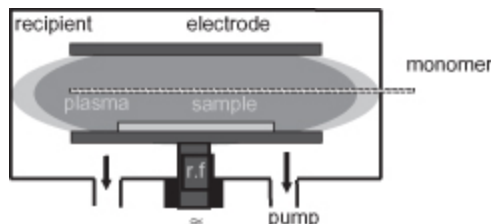

In contrast, the plasma bombardment of polymer surfaces (cf. Figure 1.3) is an efficient, easy, clean, comfortable, and fast way to create reactive centers at which plasma gas fragments or atoms can stick as new functional groups. The

processes starts, again, with desorption and functionalization and is continued by modification of near-surface layers, etching at the surface, and photo-modification of far-from surface layers considering an overlap of all processes. The surface functionalization is limited to an O/C ratio of about 0.28; a steady-state process between continuation of introduction of functional groups and polymer etching is then established. The maximum density of functional groups at the outermost polymer surface is completed after a few seconds, most often after only 2 s [20]. Limiting the plasma exposure to such short treatment protects the polymer surface against undesired advanced degradation and formation of defects. Moreover, applying minimal energy also preserves the original polymer structure. *Preservation of original polymer structure is always the best guarantee for maximum mechanical properties* and chemical integrity.

Unfortunately, the average and, especially, the maximal energy level of plasma particles and radiation, particularly that of electrons, is about an order of magnitude higher than that of the binding energies in polymers. Thus, plasma chemistry in a low-pressure glow discharge is equivalent to chemistry with a high excess of energy. This discrepancy is the most important hindrance to polymer modification by the use of plasma. Moreover, the plasma energy is continuously delivered as electrical current from a power plant and introduced into the plasma from the electrical power supply. Therefore, the electrically produced plasma is effectively an inexhaustible source of energy/enthalpy.


The list of binding energies for different chemical bonds (in kJ mol^{-1}) at 100 kPa and 298 K reflects the situation in polymers: $\text{HC}\equiv\text{CH}$ (963), $\text{N}\equiv\text{N}$ (950), $\text{H}_2\text{C}=\text{CH}_2$ (720), $\text{N}=\text{N}$ (418), $\text{O}=\text{O}$ (498), $\text{N}-\text{N}$ (163), $\text{H}_3\text{C}-\text{CH}_3$ (368), $\text{H}-\text{C}_2\text{H}_5$ (410), $\text{H}-\text{CH}_3$ (435), $\text{H}-\text{CCl}_3$ (402), $\text{H}-\text{C}_6\text{H}_5$ (460), $\text{H}-\text{CH}_2\text{OH}$ (402),

H-Cl (431), H-OCH₃ (440), H-N(CH₃)₂ (398), and C-O (358) (3-6 eV binding energy). These binding energies match exactly the average energies in electrical glow discharges working at low pressures in the range 10⁰-10³ Pa. Considering the high energy tail of the electron energy distribution function in a gas plasma ($E_{kin} = 3 \rightarrow 20$ eV) these electrons have enough energy to break all chemical bonds present in polymers (Section 4.1). It must be also considered that all electrons slowed or stopped by inelastic collisions with atoms or ions in the plasma are re-accelerated to high energies due to the applied electrical field. Thus, as noted, the plasma appears as a source of (nearly) unlimited enthalpy/energy flow.

On the other hand, plasma is a very easy tool with which to form reactive sites as radicals or functional groups independent of the inertness of polymer. In each case the plasma forms anchoring sites for further chemical reactions.

Atoms at the topmost layer of solid surfaces have generally unsaturated valences towards the gas phase. These unsaturated binding forces are responsible for the surface energy of solids. This surface energy determines wetting and gluing properties. In alkyl chains any significant dipole moment is absent; thus, polyolefins, silicones, or perfluorinated polymers have very low surface energies, composed of the dispersion component without an appreciable polar component. The introduction of functional groups forms dipoles at the surface and, thus, the polar component of the surface energy is increased strongly, as presented schematically in Figure [1.6](#) on an atomic level.

[Figure 1.6](#) Schematics of polymer surfaces.

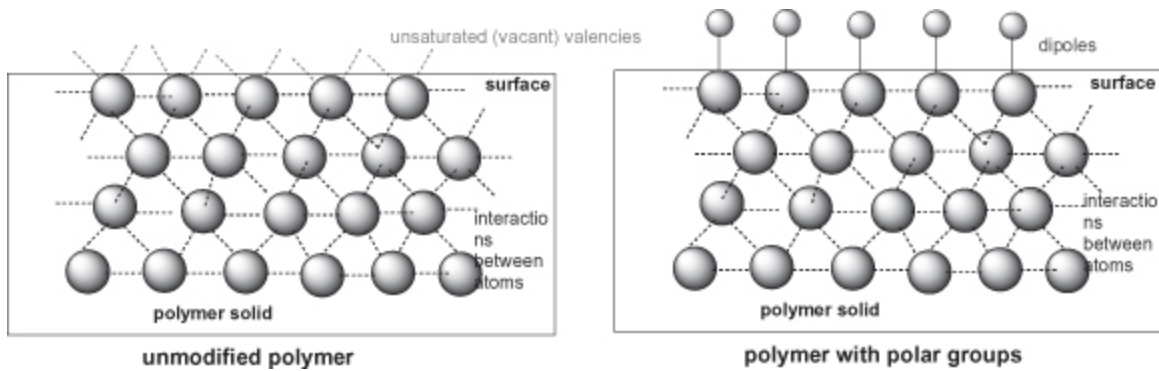

Drost, McTaggart, and Venugopalan, illustrated several traditional atmospheric and low-pressure glow discharge processes in industry [19, 21, 22]. Polyolefin or polymer modifications by surface functionalization were performed in atmospheric-pressure plasmas (corona, barrier, and glow discharges) [23] or low-pressure glow discharges [4]. This is because of the non-isothermal (non-equilibrium, nt) character of such plasmas, which show low gas temperatures (“cold” plasma) [24]. Thus, both the atmospheric and low-pressure plasmas were generally suited for any polymer pretreatment. Very fast and continuous corona or barrier discharge treatments of polymer foils at atmospheric pressure are traditional plasma applications to polymers on an industrial scale [25, 26]. However, the field of applications of this atmospheric plasmas enlarged slowly because the surface modification could not be well-controlled, is afflicted with a few inhomogeneities, and degraded material (LMWOM) is formed. More recently, the atmospheric-pressure glow discharge (APGD) has compensated these disadvantages [27, 28]. The non-selective surface functionalization accompanied by uncontrolled degradation need not be accepted, as demonstrated by use of the newly developed atmospheric-pressure plasma techniques, such as aerosol barrier discharge and electrospray ionization (ESI) film deposition [15].

The improved new plasma pretreatments aim to favor the introduction of (most advantageously: monosort) functional groups onto the surface to enhance the interactions to coatings or biomolecules or to form anchoring points for further graft synthesis. In addition, surface roughening, crosslinking of surface-near polymer layers, polymer etching, polymer ashing, and so on are also being examined by the plastic and electronic industries and in medical techniques.

Considering the use of plasma for adhesion promotion in more detail, the more ambitious improvement of metal adhesion to polymers demands the application of low-pressure glow discharge plasmas. The polyfunctional O-containing groups are rapidly produced on exposure to the oxygen low-pressure plasma. However, polymer degradation products at the interface of a polymer-metal composite hinder the adhesion by forming a “weak boundary layer” (WBL) [29] that originates from the LMWOM. This “debris” hinders adhesion to solid-phase metal layers. In contrast, liquid paints or glues can assimilate these loosely bonded fragments, dissolve and distribute them in the liquid phase of the adhesive. Thus it does not strongly hinder the adhesion between the coating and the polymer. Now, the coating can interact directly with the non-degraded polymer surface (Figure [1.7](#)). Roughening and crosslinking as well as plasma-chemical deposition of a thin adhesion-promoting interlayer are alternatives (Figure [1.8](#)).

[Figure 1.7](#) Schematic representation of a polyethylene surface before and after plasma treatment as well as after coating with a viscous adhesive.


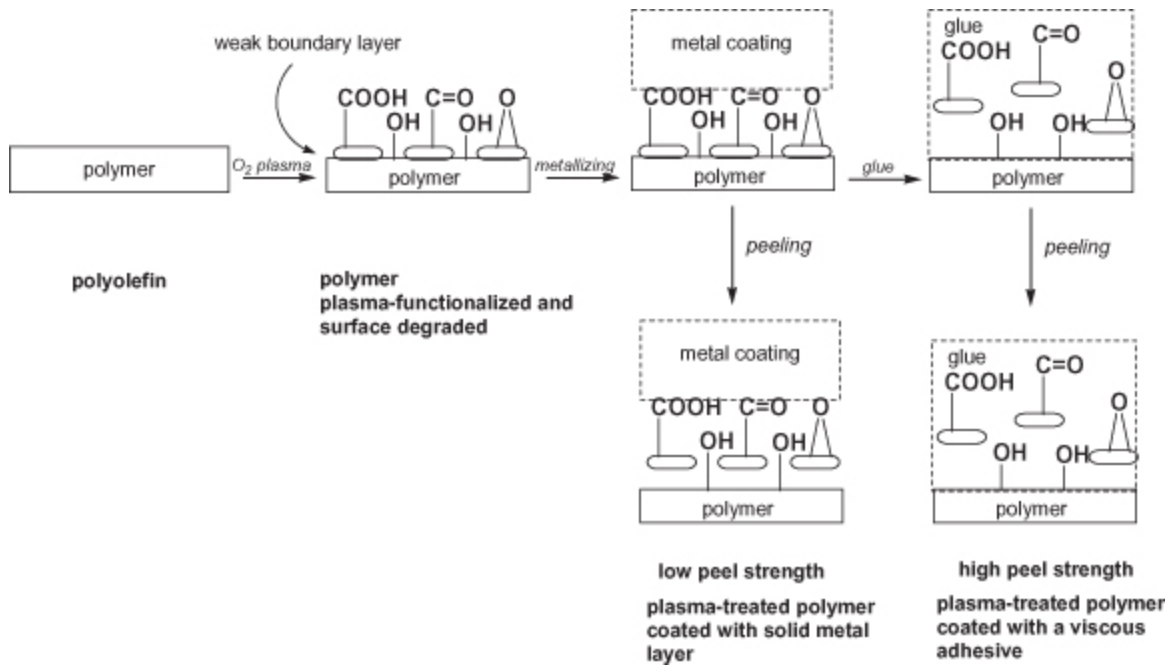



Figure 1.8 Schematics of adhesion promotion in polymer composites using the plasma technique.

Surface modification


ideal modification




too strong modification

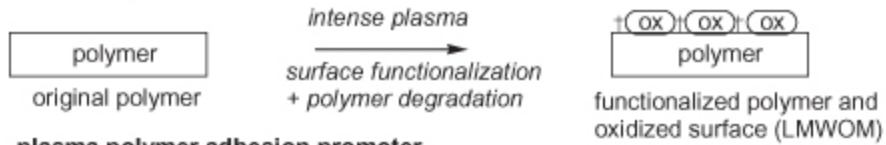

plasma polymer adhesion promoter

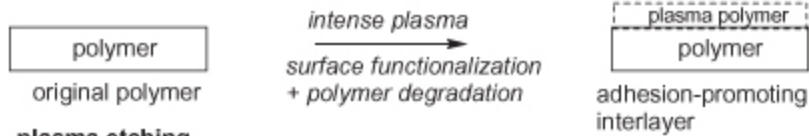


plasma etching

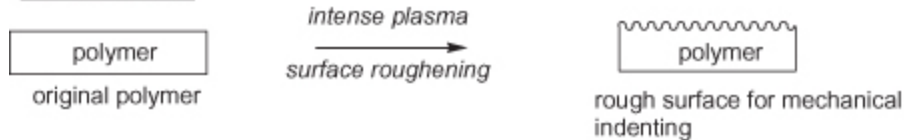


Composite interface


covalent or physical bonding

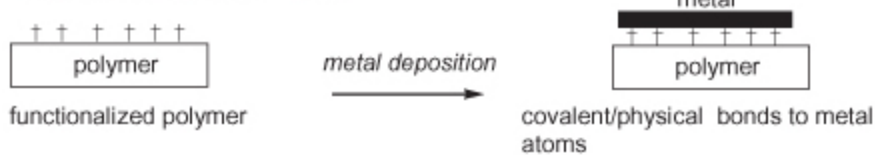

worse adhesion by WBL

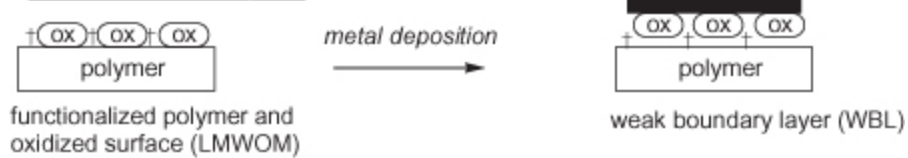

good adhesion in spite of WBL

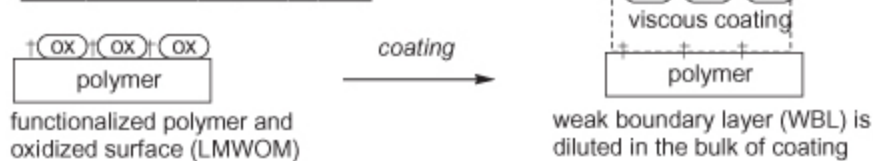

References

1 van der Waals, J.D. and Kohnstamm, P. (1908) *Lehrbuch der Thermodynamik: Teil 1*, Johann-Ambrosius Barth Verlag.